

# Spin-lattice relaxation in cerium magnesium nitrate at helium temperatures : a new process

Autor(en): **Finn, C.B.P. / Orbach, R. / Wolf, W.P.**

Objektyp: **Article**

Zeitschrift: **Archives des sciences [1948-1980]**

Band (Jahr): **13 (1960)**

Heft 9: **Colloque Ampère**

PDF erstellt am: **21.07.2024**

Persistenter Link: <https://doi.org/10.5169/seals-738553>

## **Nutzungsbedingungen**

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern. Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden. Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

## **Haftungsausschluss**

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.

## Spin-lattice Relaxation in Cerium Magnesium Nitrate at Helium Temperatures: A new process \*

by C. B. P. FINN, R. ORBACH \*\* and W. P. WOLF

---

We have made measurements of the spin-lattice relaxation time,  $T_1$ , of a single crystal of  $Ce_2Mg_3(NO_3)_{12} \cdot 24H_2O$ , using the method of Casimir and du Pré [1], at frequencies between 175 c/s and 900 c/s and d.c. fields of 300, 600 and 1000 oersteds. In all fields an extremely rapid variation of  $T_1$  with temperature was observed, (see Fig. 1),  $T_1$  increasing by a factor of about 350 between 3°K and 1.9°K. Outside this temperature range the limited frequencies available to us at the time prevented quantitative measurements, but the trend indicated that  $T_1$  varied much less rapidly between 1.9°K and 1.1°K. Above 3°K,  $T_1$  seemed to continue its rapid variation, because no paramagnetic resonance absorption was observed above 10°K even at  $10^{10}$  c/s [2].

To interpret these results we have concentrated on measurements at relatively high fields; for these it is a good approximation to neglect spin-spin interaction effects compared with the Zeeman splittings [2]. There are no complications from nuclear hyperfine structure or small Stark splittings  $\sim kT$ , and, under these conditions, the salt behaves very much like an assembly of ideal  $S = 1/2$  spins save for an anisotropic  $g$ -value. There is, however, one important additional factor: specific heat [3] and susceptibility [4] measurements have shown that there is an excited energy state ( $|J_z = \pm 3/2\rangle$ ) relatively close to the ground doublet ( $\Delta/k = 34^\circ K$ ) and we suggest that this dominates the relaxation between the components of the ground state doublet in the temperature range covered by our experiments.

In the usual treatment of spin-lattice relaxation [6], as applied to salts of the iron group, one considers excited states at energies which are much larger than the maximum phonon energy  $\sim k\theta_D$ . Hence there are no

\* Supported in part by the U.S. Air Force Cambridge Research Center through the European Office of A.R.D.C.

\*\* National Science Foundation Postdoctoral Fellow.

simple spin-phonon processes with energy sufficient to cause real transitions to the excited states, and relaxation proceeds by second and higher order processes involving spin-orbit and orbit-lattice interactions. However, if  $\Delta \ll k\theta_D$  [6], real phonon-induced transitions to the excited states become possible and relaxation of the ground state doublet can occur by a two stage process, each *step* of which is a single phonon (or 'direct') process [7]. (See Fig. 2). At temperatures at which  $kT \ll \Delta$ ,  $T_1$  due to such a mechanism should vary as  $e^{\Delta/kT}$ . Comparison with the experimental results (Fig. 1) shows that this is exactly what is observed between 3°K and 2°K. The slopes of the lines of  $\log T_1$  versus  $1/T$  are  $34 \pm 1^\circ\text{K}$ , in good agreement with the value  $\Delta/k \cong 34^\circ\text{K}$  deduced from specific heat and susceptibility.

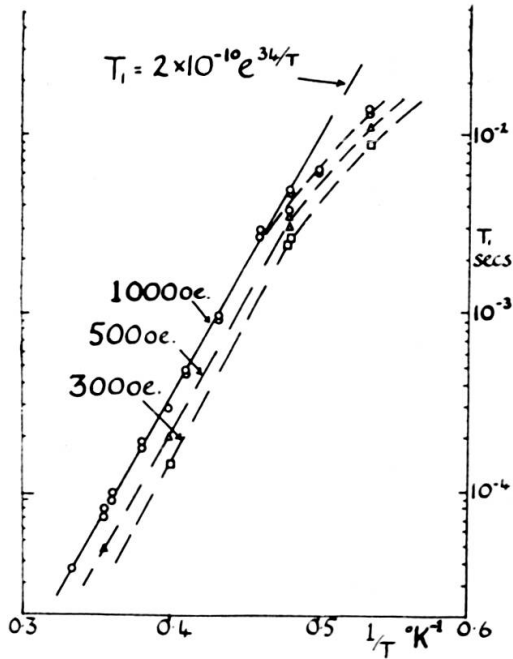


Fig. 1.

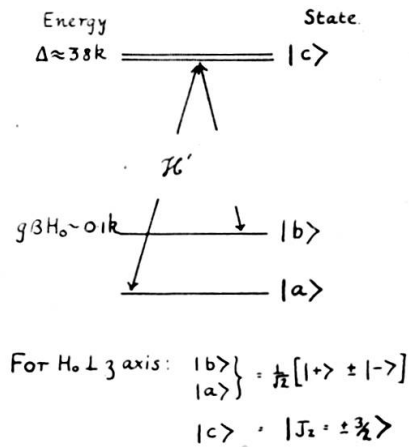


Fig. 2.

The absolute magnitudes of relaxation times in rare earth salts are in general very short, since the magnetic states are functions of  $J = L + S$ , and are therefore directly coupled to the lattice by crystalline fields. We calculate the magnitude of  $T_1$  for the two phonon process described above by using as an approximate estimate of the orbit-lattice interaction the Hamiltonian  $H_{OL} = (V_2^1 + V_4^1)\epsilon$ , where  $\epsilon$  is the strain and  $V_2^1$  and  $V_4^1$

are terms in the crystalline field potential as defined by Stevens [8]. We find, apart from spin-spin effects,

$$\frac{1}{T_1} \approx \frac{3}{2\hbar\rho v^5} \left| \left\langle \text{ground doublet} \left| V_2^1 + V_4^1 \right| \text{excited state} \right\rangle \right|^2 \left( \frac{\Delta}{\hbar} \right)^3 e^{-\Delta/kT},$$

where  $\rho$  is the density and  $v$  is the phonon velocity. Estimating  $V_2^1$  and  $V_4^1$  from the work of Judd [9] and letting  $\Delta/k = 34^\circ\text{K}$ ,

$$T_1 \sim 10^{-10} e^{34/T} \text{ secs.},$$

in very satisfactory agreement with experiment. It is to be pointed out that at higher temperatures the usual Raman processes may become more important than our two stage process because of virtual transitions to and from the second excited state for which  $\Delta/k \sim 200^\circ\text{K}$  [4]. For  $T < 1.8^\circ\text{K}$  the normal direct process would appear to become more important. Over a limited temperature range, however, we find the presence of the low lying excited state to be all important and to give rise to the dominant relaxation mechanism.

We wish to thank Dr. R. J. Elliott for many helpful suggestions and Professor J. H. Van Vleck and Dr. A. H. Cooke for stimulating discussions.

#### REFERENCES

1. CASIMIR, H. G. B. and F. K. DU PRÉ, *Physica*, 5, 507 (1938).  
CASIMIR, H. G. B., D. BIJL and F. K. DU PRÉ, *Physica*, 8, 449 (1941).  
BENZIE, R. J. and A. H. COOKE, *Proc. Phys. Soc.*, A 63, 201 (1950).
2. COOKE, A. H., H. J. DUFFUS and W. P. WOLF, *Phil. Mag.*, 44, 623 (1953).
3. C. A. BAILEY, to be published.
4. LEASK, M. J. M. and W. P. WOLF, to be published.
5. VAN VLECK, J. H., *Phys. Rev.*, 57, 426 (1940).
6. Low Temperature Specific Heat Measurements (C. A. BAILEY, *Phil. Mag.*, 4, 833, 1959) indicate that  $\theta_D \sim 60^\circ\text{K}$ .
7. It has been pointed out by Dr. B. Bölger (private communication) that a similar process has been put forward by J. P. LLOYD and G. E. PAKE, *Phys. Rev.*, 94, 579 (1954) in quite a different context. We are indebted to Dr. Bölger for this communication.
8. STEVENS, K. W. H., *Proc. Phys. Soc.*, A 65, 209 (1952).
9. JUDD, B. R., *Proc. Roy. Soc.*, 232, 458 (1955).