

# The relations $M_{st}(P)$ and $M_{F}(P)$ in girders continuous over three spans carrying a load $P$ in the central span

Autor(en): **Maier-Leibnitz, H.**

Objektyp: **Article**

Zeitschrift: **IABSE congress report = Rapport du congrès AIPC = IVBH  
Kongressbericht**

Band (Jahr): **2 (1936)**

PDF erstellt am: **21.07.2024**

Persistenter Link: <https://doi.org/10.5169/seals-3245>

## **Nutzungsbedingungen**

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

## **Haftungsausschluss**

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.


The Relations  $M_{st}$  (P) and  $M_F$  (P) in Girders Continuous over Three Spans Carrying a Load P in the Central Span  
(see Preliminary Publication, pages 121–126).<sup>1)</sup>

Die Beziehungen  $M_{st}$  (P) und  $M_F$  (P) beim durchlaufenden Balken mit drei Öffnungen, belastet durch P im Mittelfeld (siehe Vorbericht Seite 126–128).<sup>1)</sup>

Les expressions  $M_{st}$  (P) et  $M_F$  (P) dans la poutre continue à trois ouvertures, soumise à une charge P agissant dans la travée médiane (voir la Publication Préliminaire, pages 121–126).<sup>1)</sup>

Dr. Ing. H. Maier-Leibnitz,  
Professor an der Technischen Hochschule, Stuttgart.

If the girder shown in Fig. 1 be subjected to a load increasing from 0 to P the first result is a bending moment diagram calculable from purely elastic

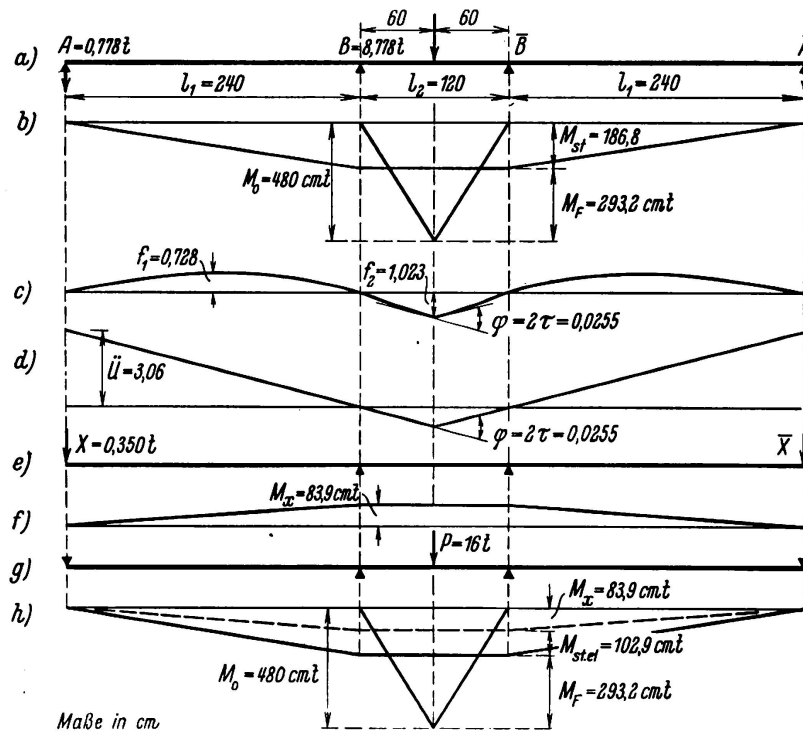

Maße in cm  
= Scale in cm  
Fig. 1.  
Behaviour of girder under a load P = 16 tonnes.

<sup>1</sup> See also the journal „Der Stahlbau“, 1936, No. 20, pp. 153 foll.

principles and characterised by  $M_o$ ,  $M_{st}$ ,  $M_F$ . When  $P = P_s$  ( $\approx 11$  tonnes) the yield stress  $\sigma_s$  is attained at the extreme fibre in the middle of the span.

As soon as  $P > P_s$  (as, for instance, when  $P = 16$  tonnes),  $M_F$  cannot increase appreciably above  $M_s = W \cdot \sigma_s$ . With the aid of *Mohr's* theorem an expression for the angle  $\varphi$  of the line of bending at the middle of the girder can be derived by considering the line of moments (Fig. 1b) from A to B and from B to the point where the line of bending has a kink. In the present case

$$EI\varphi = 6600 P - 280 M_F.$$

If the load is removed the shape of the beam in Fig. 1d shows at the ends an amount  $\ddot{u}$ , and before the load is re-imposed  $\ddot{u}$  has to be eliminated by the two

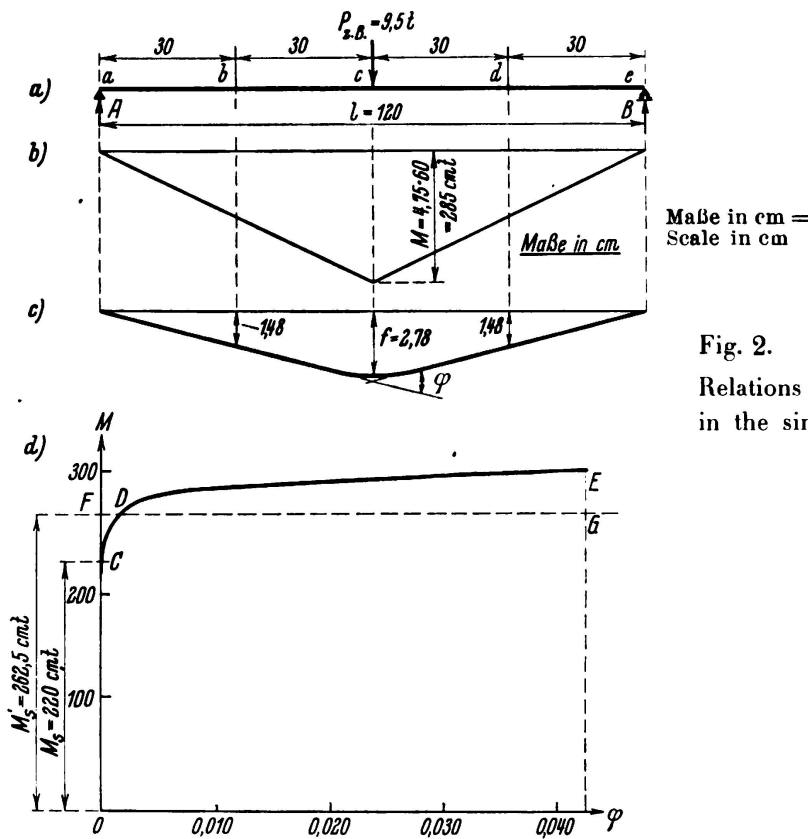


Fig. 2.  
Relations of  $\varphi(M)$   
in the simple beam.

forces  $X$  and  $\bar{X}$  corresponding to the moments at the supports  $M_x$ . On reloading with  $P = 16$  tonnes,  $M_x$  is augmented by the purely elastic support-moment  $M_{st,el}$  (line of moments corresponding to Fig. 1h).

How great is  $M_F$  and, therefore, the support moment  $M_{st} = M_o - M_F$  and the values of  $\varphi$ ,  $\ddot{u}$  and  $X$ ?

In a simple beam, for instance in the beam of comparison  $l = 120 \text{ cm} = l_2$  the relation  $\varphi(M)$  may be obtained by purely experimental means as shown in Fig. 2, where  $M$  is the moment at the middle of the beam. In order to indicate the actual behaviour of the continuous beam this relationship may be transferred to the continuous beam, that is to say  $M_{(\varphi)} = M_F(\varphi)$ . On the other hand we may write the relationship stated above:

$$EI\varphi = 6600 P - 280 M_F$$

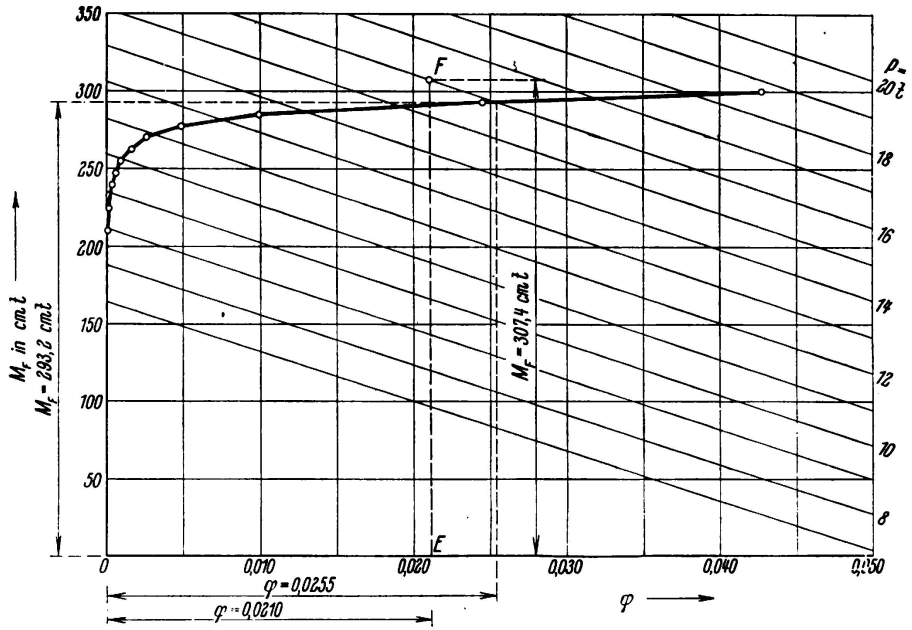


Fig. 3.

Determination of  $M_F$  for  $l_1 = 240$  cm and  $l_2 = 120$  cm, with the aid of  $EI_\varphi = 6600 P - 280 M_F$  (particularly with  $P = 16$  tonnes).

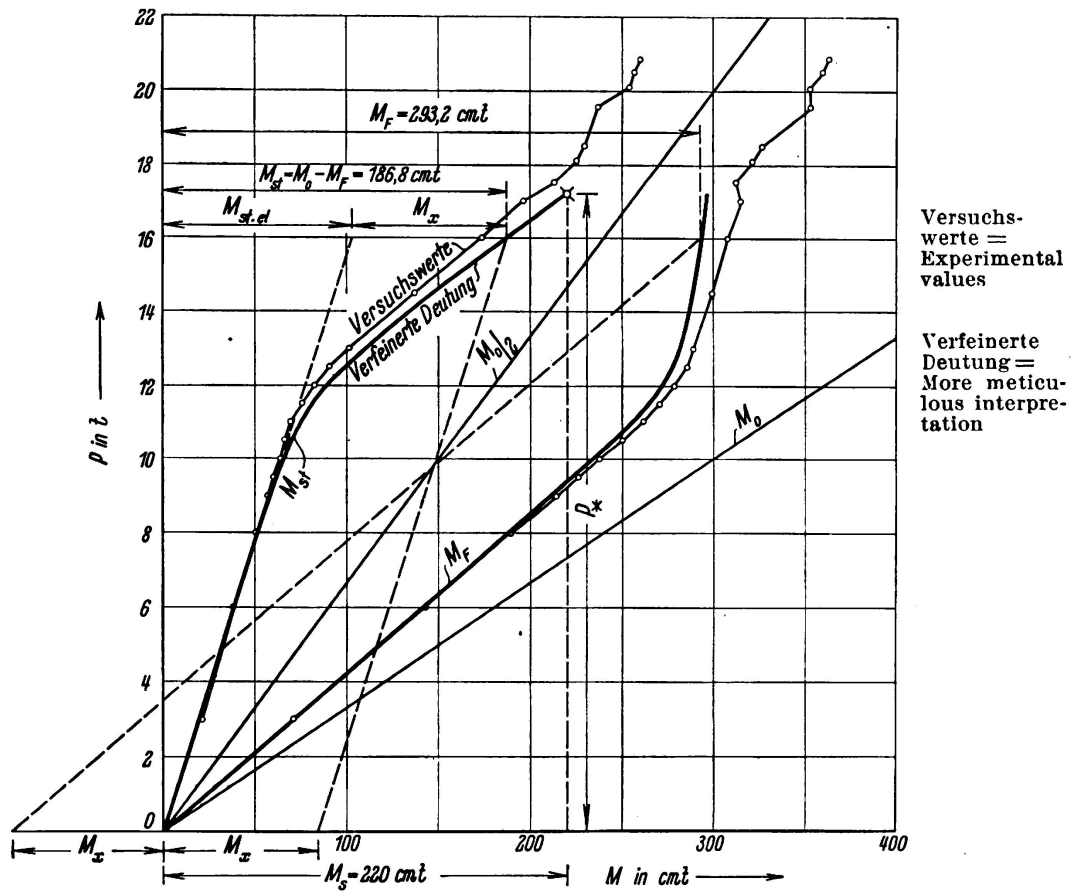


Fig. 4.

Relations  $M_{st}(P)$  and  $M_F(P)$  for  $l_1 = 240$  cm.

Fig. 3 shows both the relationships. Where  $P = 16$  tonnes we obtain  $M_F = 293.2$  cm tonnes and  $\varphi = 0.0255$  (the more precise hypothesis of interpretation).

If this determination is effected for the other loads also, we obtain the picture shown in Fig. 4.  $M_{st}$  and  $M_F$  at first increase according to linear law, then from  $P'_s = 11.12$  tonnes onwards by curves. With  $P = 16$  tonnes the values of  $M_x$  and  $M_{st,el}$  established above (Fig. 1h) are entered in the diagram. It may also be seen from this diagram how a reimposition of load takes place after removal of load, and that the values in the more exact hypothesis of interpretation agree well with the experimental values indicated by the lighter lines.

In Fig. 3 for  $P = 16$  tonnes is given the experimental value  $M_F = 307.4$  cm tonnes as the ordinate EF. The ordinates of the curve  $\varphi$  ( $M_F$ ) are, therefore, greater than those of the curve  $\varphi$  (M) which appertain to the beam of comparison with  $l = 120$  cm. This is due to the fact that reference should properly be made for shorter experimental beams of comparison with a span equal to the distance between the points where the moment in the central opening is zero; a fact which is confirmed by experiments carried out subsequently to the Congress with  $l = 950$  cm corresponding to  $P_s$  and  $l = 730$  cm corresponding to  $P_T$ .

The foregoing provides a basis for a more exact solution than has hitherto been available of the problem of the actual carrying capacity of continuous girders of structural steel, and closes a gap to which *J. Fritsche* has drawn attention in the journal *Der Stahlbau*, Vol. 9 (1936), page 67. In future, therefore, as is done in the „Traglastverfahren“ [carrying capacity method] it will not be necessary to rely upon the overprimitive assumption of equalisation of moments.