Zeitschrift: IABSE congress report = Rapport du congrès AIPC = IVBH Kongressbericht

Band: 13 (1988)

Artikel: Simulation of cyclic plasticity behaviour of structural members

Autor: Nishiwaki, Takeo / Minagawa, Masaru / Masuda, Nobutoshi

DOI: https://doi.org/10.5169/seals-13185

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Siehe Rechtliche Hinweise.

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. Voir Informations légales.

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. See Legal notice.

Download PDF: 17.05.2025

ETH-Bibliothek Zürich, E-Periodica, https://www.e-periodica.ch

Simulation of Cyclic Plasticity Behaviour of Structural Members

Simulation du comportement de plasticité cyclique d'éléments de structures

Rechnerische Simulation des zyklisch-plastischen Verhaltens von Tragelementen

Takeo NISHIWAKI
Professor
Musashi Inst. of Technology
Tokyo, Japan

Masaru MINAGAWA
Research associate
Musashi Inst. of Technology
Tokyo, Japan

Nobutoshi MASUDA
Associate Professor
Musashi Inst. of Technology
Tokyo, Japan

1.INTRODUCTION

Computer simulation of the cyclic plasticity behaviours of structures or structural members is very important to evaluate structural safety and make them safe against severe cyclic loading due to earthquakes, wind storms and so on. Here a cyclic plasticity theory for elasto-plastic hysteretic behaviours of structural steel is proposed and it is applied to the analyses of structural members subjected to cyclic loads.

2.CYCLIC PLASTICITY MODEL

The proposed model is derived by the refinements of a multi surface plasticity theory introduced by Petersson and Popov[1]. Petersson-Popov model used cumulative equivalent plastic strain as a state variable, two fundamental surface size functions and a weighting function as material property functions.

There are three important differences between Petersson-Popov model and the proposed model. Firstly, effective value of cumulative equivalent plastic strain is defined as a state variable to represent "Return Phenomena". Secondly, additional material property functions are introduced. These functions express strain hardening characteristics of materials after loading histories corresponding to certain values of cumulative equivalent plastic strain. Owing to this modification, the theory can express strain hardening characteristics of materials with both notable strain hardening and non-hardening strain region. Thirdly, all of the material property functions can easily and unambiguously be obtained by a combination of a simple tension test and several simple tension-compression tests.

3.APPLICATION OF THE MODEL

This method is applied to simulation of tension-compression stress-strain relationships of mild steel and high strength steel. Using material property functions measured, the authors carried out elasto-plastic finite element analyses for round-bar specimens subjected to repetitive tension-compression loading under controlled strain. Figure 1 shows stress-strain relationships predicted by the proposed model and those gained by the corresponding experiments. By comparing these results, it was confirmed that the stress-strain relationships calculated by the proposed theory was accurate.

A next application of the cyclic plasticity model is the evaluation of bending moment-curvature relationships(M-Φ relationships) of steel beams. In the calculation of the M-Φ relationships of beams and beam-columns by the proposed

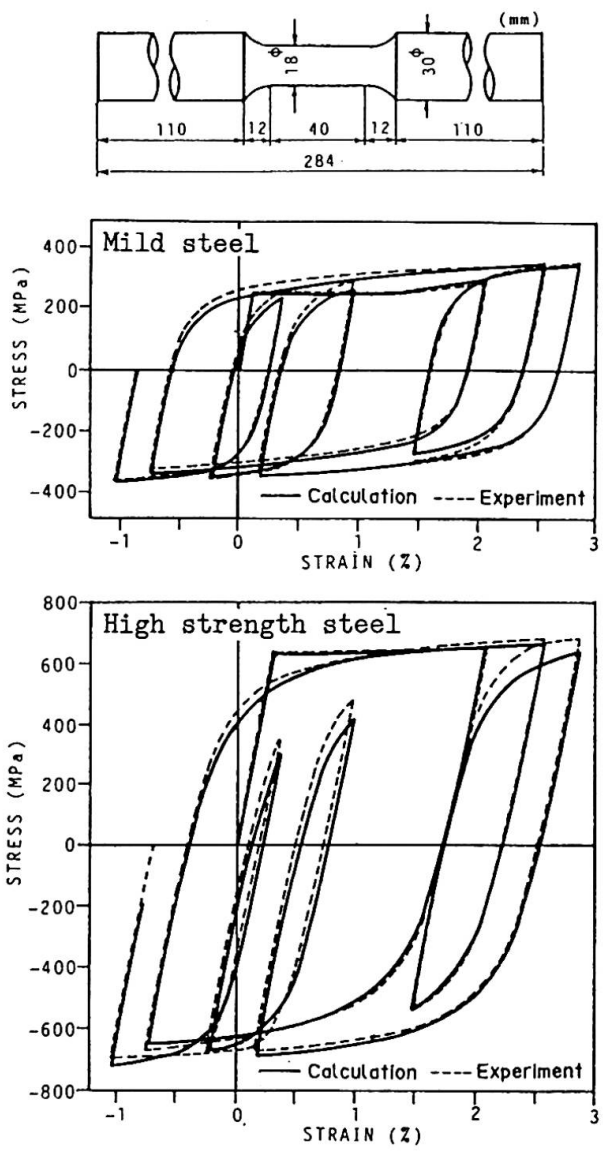

Figure 1 Stress-strain relationships of round bar specimens.

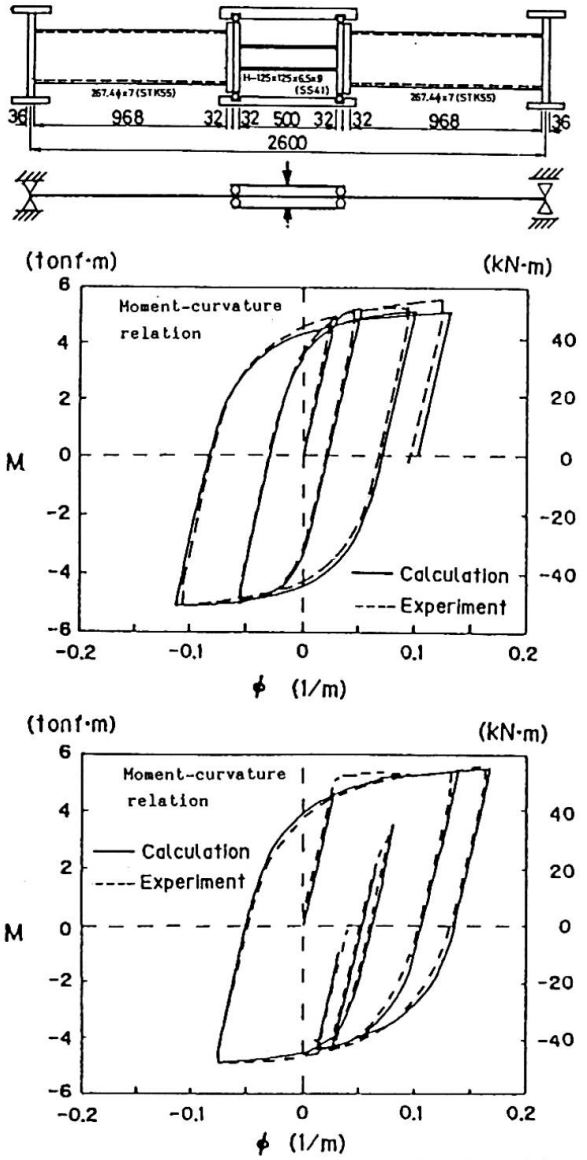

Figure 2 Moment-curvature relationships of simple beam specimens.

stress-strain model, the tangent stiffness method introduced by Chen and Atsuta[2] was used with some modifications.

JIS(Japanese Industrial Standards)-5 type specimens were shaped from a H-shaped beam specimen to evaluate material property functions. Material property functions were determined by a combination of tension tests and tension-compression tests. Residual stress characteristics were analyzed by a drilling method and simple type distribution was assumed according to these results.

The calculated M-Φ relationships are compared with those obtained by experiments which the authors had carried out. Figure 2 shows hysteretic M-Φ relationships predicted and those gained by the corresponding experiments. The accurate M-Φ relationships can be evaluated by the authors' theory.

REFERENCES

1.PETERSSON H. and POPOV E.P., Constitutive relation for generalized loadings, Proc. of ASCE, Vol.103, No.EM4, pp.611-627, 1977.
2.CHEN W.F. and ATSUTA T., Theory of Beam-Column, McGraw-Hill Inc., 1977.

Leere Seite
Blank page
Page vide