

Zeitschrift: IABSE structures = Constructions AIPC = IVBH Bauwerke
Band: 8 (1984)
Heft: C-31: Storage tanks

Artikel: LNG storage tanks in Bintulu (Malaysia)
Autor: Hamette, J. de la
DOI: <https://doi.org/10.5169/seals-18835>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften auf E-Periodica. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. Das Veröffentlichen von Bildern in Print- und Online-Publikationen sowie auf Social Media-Kanälen oder Webseiten ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. [Mehr erfahren](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. La reproduction d'images dans des publications imprimées ou en ligne ainsi que sur des canaux de médias sociaux ou des sites web n'est autorisée qu'avec l'accord préalable des détenteurs des droits. [En savoir plus](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. Publishing images in print and online publications, as well as on social media channels or websites, is only permitted with the prior consent of the rights holders. [Find out more](#)

Download PDF: 30.06.2025

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>



2. LNG Storage Tanks in Bintulu (Malaysia)

Owner: Malaysian LNG
Main contractor: Japan Gasoline Co + Pullmann Kellogg
Sub contractor: Toyo Kanetsu
Starting date: 1982

One of the most advanced designs of LNG storage tanks uses a 9 % Nickel-steel inner tank surrounded by an independent concrete confinement wall and an earthen berm as shown in fig 1. It is known as the «double-integrity» concept.


The secondary containment of such a configuration may be subjected to high peak stresses under low temperature conditions in case of an accident, as the event of a partial or total failure (zip-up) of the inner tank cannot be excluded.

It is well known that for standard reinforcing steels as used in day-to-day jobs toughness and ductility deteriorate with decreasing test temperature to a point where brittle failure will occur.

The concrete reinforcing steels for low temperature applications must therefore, in addition to the normal range of properties which characterize standard reinforcing steels, maintain a high level of ductility or toughness reserve at the low design temperature.

Recent specifications for concrete reinforcing bars used in LNG storage tanks require:

- an adequate yield-point level in combination with a minimum elongation on notched tensile specimens tested at the design temperature, if the designer expects static load conditions
- or
- an adequate yield-point level in combination with a minimum Charpy-V notch toughness at design temperature, if dynamic loading is expected.

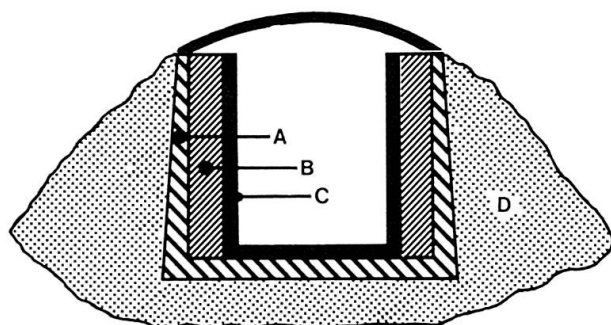

A: Concrete reinforcement walls
 B: Insulation
 C: 9 % Ni steel tank
 D: Earthen berm

Fig.1 LNG-Storage Tank

Amongst those requirements, the latter is the most stringent one and the most difficult to meet.

To satisfy such severe specifications the choice of available steel qualities is limited to Nickel-steels which normally obtain the required properties by a postrolling heat treatment consisting in a double normalization or a quenching and tempering and to austenitic steels with cryogenic properties. Both types of steel are very high-priced, due to the alloy costs and to the expensive post-rolling heat treatment.


In view of this situation and considering the market needs, Arbed developed a new production process for Krysteels that match the cryogenic properties of high Nickel alloys without or with reduced Nickel content and without need for a heat treatment after rolling or after working of the steels at site. Thus significant economy can be achieved without sacrificing cryogenic performance. This new patented production method utilizes a closely controlled chemical analysis together with a special rolling technique.

This new development has resulted in the definition of 2 reinforcing steel series which meet the requirements for cryogenic applications:

Krybar with guaranteed Charpy-V notch impact properties at -120°C (-184°F).

Krybar Ni with guaranteed Charpy-V notch impact properties at -165°C (-265°F).

The results of Charpy-V notch tests, simulating dynamic load, are summarized in the following diagrams:

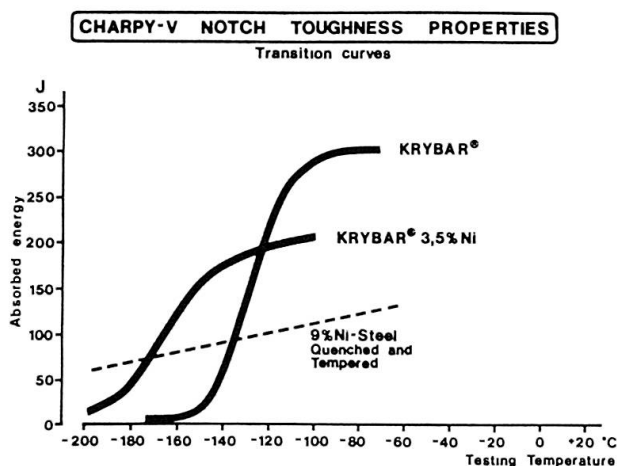

Since the original development, different material specifications have been drawn up to suit conditions peculiar to other projects i.e. ductility requirements on notched tensile bars at -165°C (-265°F).

(J. de la Hamette)

