

# Stress assessment of reinforced concrete structures with cracks

Autor(en): **Pukelis, Petras / Jokubaitis, Vidmantas / Kaminskas, Kazys Algirdas**

Objekttyp: **Article**

Zeitschrift: **IABSE reports = Rapports AIPC = IVBH Berichte**

Band (Jahr): **67 (1993)**

PDF erstellt am: **22.07.2024**

Persistenter Link: <https://doi.org/10.5169/seals-51371>

## **Nutzungsbedingungen**

Die ETH-Bibliothek ist Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Inhalten der Zeitschriften. Die Rechte liegen in der Regel bei den Herausgebern.

Die auf der Plattform e-periodica veröffentlichten Dokumente stehen für nicht-kommerzielle Zwecke in Lehre und Forschung sowie für die private Nutzung frei zur Verfügung. Einzelne Dateien oder Ausdrucke aus diesem Angebot können zusammen mit diesen Nutzungsbedingungen und den korrekten Herkunftsbezeichnungen weitergegeben werden.

Das Veröffentlichen von Bildern in Print- und Online-Publikationen ist nur mit vorheriger Genehmigung der Rechteinhaber erlaubt. Die systematische Speicherung von Teilen des elektronischen Angebots auf anderen Servern bedarf ebenfalls des schriftlichen Einverständnisses der Rechteinhaber.

## **Haftungsausschluss**

Alle Angaben erfolgen ohne Gewähr für Vollständigkeit oder Richtigkeit. Es wird keine Haftung übernommen für Schäden durch die Verwendung von Informationen aus diesem Online-Angebot oder durch das Fehlen von Informationen. Dies gilt auch für Inhalte Dritter, die über dieses Angebot zugänglich sind.


**Stress Assessment of Reinforced Concrete Structures with Cracks**  
Estimation des contraintes des constructions en béton armé fissurées  
Spannungsermittlung in gerissenen Stahlbetontragwerken

**Petras PUKELIS**  
Associate Professor  
Vilnius Technical University  
Vilnius, Lithuania




Petras Pukelis, born 1932, received his diploma of civil engineer and candidate of science degree at Kaunas Technological University, Kaunas, Lithuania. His scientific interests are shear strength of reinforced concrete, evaluation and strengthening of structures of existing buildings.

**Vidmantas JOKUBAITIS**  
Associate Professor  
Vilnius Technical University  
Vilnius, Lithuania

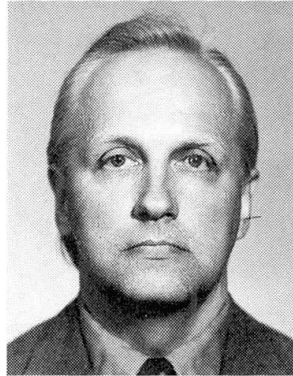

Vidmantas Jokubaitis, born 1938, received his diploma of civil engineer and candidate of technical science degree at Kaunas Technological University, Kaunas, Lithuania. Main area of his research activity is evaluation of reinforced concrete structures with cracks of existing buildings.

**Kazys Algirdas KAMINSKAS**  
Associate Professor  
Vilnius Technical University  
Vilnius, Lithuania

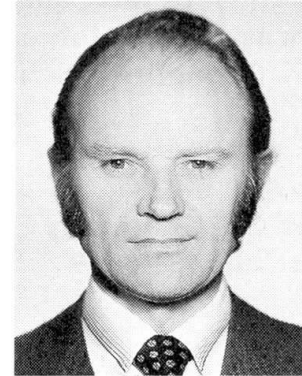

Kazus Algirdas Kaminskas, born 1940, received his diploma of civil engineer and candidate of technical science degree at Kaunas Technological University, Kaunas, Lithuania. For twenty years he was involved in prestressed concrete and strengthening of reinforced concrete structures.

#### SUMMARY

A new method to evaluate stress in tensile reinforcement and compressed concrete of reinforced concrete members is proposed. The method is based on principles of crack propagation theory in brittle bodies. The stresses are estimated by taking into account external force action and the parameters of cracks.

#### RÉSUMÉ

L'article propose une méthode précise de calcul des contraintes d'armature longitudinale tendue et du béton comprimé dans des éléments en béton armé. On détermine les contraintes sur la base des efforts externes et des paramètres de la fissure normale. La méthode de calcul se base sur la théorie linéaire de rupture mécanique dans un corps fragile.

#### ZUSAMMENFASSUNG

Es wird eine relativ genaue Methode vorgeschlagen, um bei bestehenden Stahlbetontragwerken die Zugs- und Druckspannungen in gerissenen Querschnitten zu ermitteln. Basierend auf der linearen Bruchmechanik für spröde Körper werden die einwirkenden Kräfte und Kenngrößen der Biegerisse berücksichtigt.



## 1. INTRODUCTION

Evaluation of existing reinforced concrete structures is very important for maintenance, renovation and reconstruction of industrial and other in-service buildings. There are several methods to evaluate stress and strains in structures using their examination data. In the case of reinforced concrete structures with normal cracks in tensile zone it is possible to evaluate stress by the crack parameters measured during the examination of these structures. The degree of crack development is considered as a result of existing stress - strain state in the member [1]. In this paper a possibility to employ classical theory of crack propagation in a brittle body for calculation of tensile reinforcement stresses at the cross section through crack is investigated.

## 2. REINFORCEMENT AND CONCRETE STRESSES IN CROSS SECTION THROUGH CRACK

Within the limits of assumed model of a brittle body in the case of macroscopic cracks the following equation is valid [2]:

$$\lim_{s \rightarrow 0} \{ \sqrt{s} \sigma_{y(s,p)} \} = \frac{K}{\pi} \quad (1)$$

where  $s$  is the distance of body points situated in the crack plane from the top of the crack;  $\sigma_{y(s,p)}$  is breaking stress for a member with macroscopic crack of  $2l_0$  length and  $K$  is modulus of bond. It is shown in [2] that stresses in body outside the crack ( $x > l$ ) due to any normal pressure acting in the banks of this crack may be expressed by formula, see Fig.1(a):

$$\sigma_{y(x,0)} = \frac{1}{\pi \sqrt{x^2 - l^2}} \int_{-1}^1 \frac{p_n(\xi) \sqrt{l^2 - \xi^2}}{x - \xi} d\xi \quad (2)$$

Due to limitation of stress  $\sigma_{y(x,0)}$  in the body for the case of  $x \rightarrow l$  the following equation must be observed:

$$\lim_{x \rightarrow l} \int_{-1}^1 \frac{p_n(\xi) \sqrt{l^2 - \xi^2}}{x - \xi} d\xi = 0 \quad (3)$$

Boundary conditions for the function of the normal pressure  $p_n(\xi)$  in the tensile zone of a reinforced concrete member, see Fig.1(a), may be written as follows:

$$p_n(\xi) = \begin{cases} p_0(\xi) & |\xi| \leq c \\ 0 & |\xi| \leq l_0 - c \\ -f_{ct} & l_0 < -x \leq 1 \\ -\frac{\sigma_s \beta}{\alpha} & l_0 < x \leq 1 \end{cases} \quad (4)$$

where  $p_0(\xi)$  is arbitrary function of pressure applied on banks of the crack and estimated as a resultant of stresses acting in

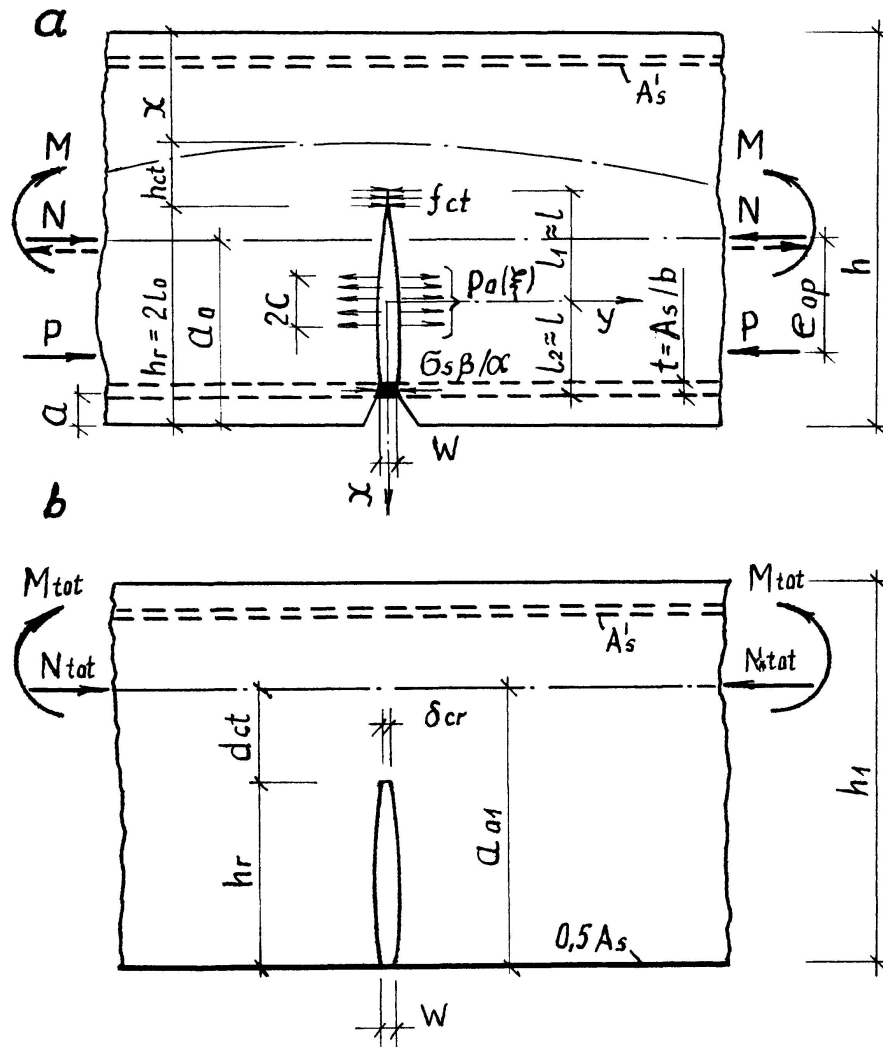


Fig.1 Models of normal crack in tensile zone of reinforced concrete member: a - for evaluation of reinforcement stress intensity coefficient; b - for assesment of tensile reinforcement stress in crack

continuous concrete of the crack zone  $|x| \leq l$ ;  $f_{ct}$  is tensile strength of concrete;  $\sigma_s \beta / \alpha$  is stress at the level of tensile reinforcement;  $\alpha = E_s / E_c$ ;  $\beta = 125 \rho$  and is used when longitudinal reinforcement ratio  $\rho = A_s / (bd)$  is small when  $\rho \geq 0.008$ ,  $\beta = 1$ .

Using equation (4) and considering that  $s = x - l_0$ ,  $\sqrt{x^2 - l_0^2} = \sqrt{s} \sqrt{l_0 + s}$ , equation (3) may be rearranged into the following form

$$\lim_{s \rightarrow 0} \{\sqrt{s} \sigma_{y(s,p)}\} \approx \frac{2\sigma_s \beta}{\alpha \pi} \sqrt{t} \quad (5)$$

From equations (1) and (5) tensile reinforcement stress

$$\sigma_s = \frac{K\alpha}{2\beta\sqrt{t}} \quad (6)$$



and critical steel stress intensity factor

$$K_{cr} = 1.6 f_s \sqrt{t} \frac{\beta}{\alpha} \quad (7)$$

where  $f_s$  is strength (yield limit) of reinforcement steel. Values greater than critical  $K_{cr}$  values leads to the fracture of not overreinforced concrete member with tensile steel.

By similar method as in [2] assuming bodies as isotropic expression of the modulus of bond  $K$  for reinforced concrete member has been deduced. A fictitious cross section of the depth  $h_f$  was assumed, see Fig.1(b), the centroid of which coincides with the central axis of the member. The depth  $h_f$  is obtained from the following expression:

$$h_r + h_{ct} = \frac{S_1}{A_1} \quad (8)$$

where  $S_1$  is statical moment of fictitious cross - sectional area  $A_1$  in respect to the centroid of longitudinal tensile reinforcement.

Modulus

$$K = \left( \frac{M_{tot} - \Delta M}{W_1} - \frac{N_{tot}}{A_1} \right) \sqrt{h_r} \frac{\pi}{2} \quad (9)$$

where  $M_{tot} = M - Pe_{op}$  and is the total moment in relation to the centroid of the real cross section of the member, see Fig.1;  $P$  is longitudinal reinforcement prestressing force;  $e_{op}$  is the eccentricity of  $P$ ;  $\Delta M = N_{tot} (a_{o1} - a_o)$  and is the increase in bending moment due to deviation of centroid of fictitious cross section from the centroid of the real cross section of the member;  $N_{tot} = P \pm N$  and is the total longitudinal force acting in the centroid of the real cross section. Compressive  $N$  force is positive;  $W_1 = I_f / (0.75h_r + h_{ct})$  and is modulus of cross section;  $I_f$  is inertia moment of fictitious cross section in relation to the neutral axis situated at distance  $h_r + h_{ct}$  from the tensile face of fictitious cross section;  $h_{ct} = \delta_{cr} h_r / w$  and is the depth of concrete tensile zone above the crack, see [1].

The critical width of the crack end

$$\delta_{cr} = 0.00012 a \sqrt[3]{\phi} \eta \frac{3.5 - 100 \rho_1}{3.5 - 100 \rho_2} \quad (10)$$

where  $\phi$  is bar diameter of tensile reinforcement in mm;  $\eta$  is factor for consideration of bond between concrete and reinforcing steel;  $\rho_1 = A_s / [bh + (b_f - b)h_f] \leq 0.02$  and  $\rho_2 = A_s / (bh) \leq 0.02$  and they are longitudinal reinforcing factors;  $b_f$  and  $h_f$  are width and the thickness of the flange in the tensile zone of the member.

Substitution of modulus  $K$  value by (9) into formule (6) gives the final expression of tensile reinforcement stress value

$$\sigma_s = \left[ \frac{(M_{tot} + \Delta M)(0.75h_r + h_{ct})}{I_1} - \frac{N_{tot}}{A_1} \right] \frac{\pi\alpha}{4\beta} \sqrt{\frac{h_r}{t}} \quad (11)$$

If the neutral axis is located extreme compressed concrete fiber stress  $\sigma_c$  may be calculated by the equation:

$$\sigma_c = \frac{M (h - h_r - h_{ct})}{I_{red}} \quad (12)$$

where  $I_{red}$  is inertia moment about neutral axis of transformed cross section by reducing its area by  $A_{ct} = h_r b$ .

For concrete coefficient

$$K_{cr} = \sqrt{\delta_{cr} E_c f_{ct}} \quad (13)$$

where  $E_c$  and  $f_{ct}$  are modulus at elasticity and tensile strength of concrete respectively.

### 3. RESULTS OF EXPERIMENTAL INVESTIGATION

Special test specimens, beams and eccentrically compressed reinforced concrete members, were investigated. Prestressed concrete beams of rectangular cross section  $b \times h = 100 \times 180 \text{ mm}$ , span  $l = 1800 \text{ mm}$ , longitudinal prestressing steel ratio  $\rho = 0.8 - 0.95 \%$ , prestressing force  $P = 41.2 - 132.5 \text{ kN}$  were subjected to two concentrated forces at 1/3 distances from supports. Electrical resistance gauges were used to measure steel strain in the cross section through crack. The parameters  $h_r$  and  $w$  of crack in pure bending zone of beams were measured by 24 times magnifying microscope and controlled by electrical resistance strain gauges closely spaced on beam face along its height.

Results of special tests on beams reported in [3] also are employed to evaluate theoretical propositions of this paper. Reinforced concrete beams of rectangular cross section  $b \times h = 120 \times 300 \text{ mm}$ , span length  $l = 2000 \text{ mm}$ , longitudinal tensile reinforcement ratio  $\rho = 0.48 - 3.83\%$ , without prestress were loaded by two concentrated forces at 1/3 distances from supports. Special notches were formed in the test beams to locate the main cracks. Steel strain in the main crack and parameters  $h_r$  and  $w$  of this crack were measured.

Eccentrically compressed members of rectangular cross section  $b \times h = 100 \times 150 \text{ mm}$ , length  $l = 1000 \text{ mm}$ , tensile reinforcement ratio  $\rho = 0.46 - 1.26\%$  were tested by the authors of this paper. Notches in the middle of the member length from tensile face up to longitudinal reinforcing bars deep were formed. Crack parameters were measured by a microscope magnifying 24 times and by a dial gauge at the level of tensile reinforcement.



The values of tensile reinforcement stresses obtained by tests  $\sigma_{s,obs}$  and calculated by equation (11)  $\sigma_s$  are compared, see Fig.2. In the case of eccentrically compressed

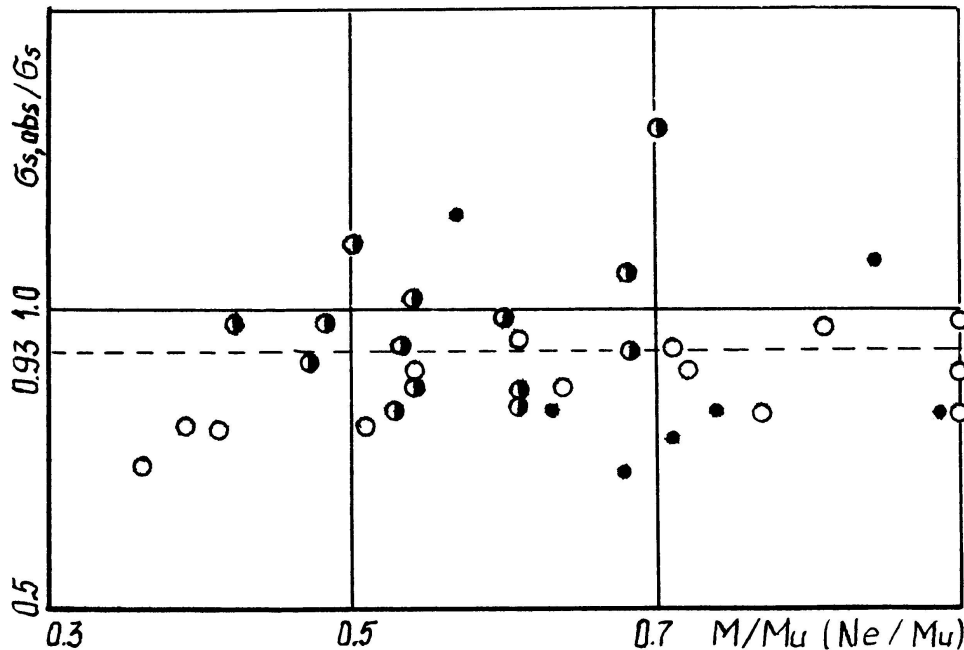


Fig.2 Comparison of measured in tests  $\sigma_{s,obs}$  and theoretical  $\sigma_s$  calculated by formula (11) tensile reinforcement stress values: • - prestressed concrete beams; o - reinforced concrete beams; ● - eccentrically compressed members

members ratio  $\sigma_{s,obs}/\sigma_s$  is plotted in respect to quantity  $Ne/M_u$  where  $N$  is external force acting at distance  $e$  from centroid of tensile reinforcement and  $M_u$  is the ultimate bending moment of the cross section.

Theoretical values  $\sigma_s$  calculated by (11) are on the average 7% higher than  $\sigma_{s,obs}$  measured in tests. The variation coefficient of the ratio  $\sigma_{s,obs}/\sigma_s$  is equal to 0.15.

Experimental values of concrete extreme fiber stress  $\sigma_{c,obs}$  obtained from tests [3] were compared with theoretical values  $\sigma_c$  of this stress calculated by equation (12). Theoretical values  $\sigma_c$  on the average are 3% higher than experimental values  $\sigma_{c,obs}$  of this stress. Coefficient of variation of the ratio  $\sigma_{c,obs}/\sigma_c$  is equal to 0.11.

#### 4. CONCLUSIONS

Contour of through normal crack in tension zone of a reinforced concrete member always is contiguous to tensile concrete and to reinforcement. The latter has substantial influence on rupture strength of tensile concrete. Parameters of this strength  $K_{cr}$  and  $\delta_{cr}$  expressed by (7), (10) and (13) define correctly character of stable crack propagation observed in tested samples.

Calculation of stresses in tensile reinforcement by (11) and in extreme fiber of compressed concrete by (12) makes it possible to assess stress state of reinforced concrete structures in service with sufficient accuracy.

#### REFERENCES

1. JOKUBAITIS V., PUKELIS P., Stress - strain state estimation in existing reinforced concrete structures subjected to bending (in russian). Transactions of Lithuanian universities. Reinforced concrete structures No.12, Vilnius,1983.
2. PANASIUK V., Ultimate equilibrium of brittle bodies with cracks (in russian). Kijev, 1968.
3. CHUBRIKOV V., Criteria of fracture mechanics for stress assesment in reinforced concrete bending member section with crack (in russian). Lvov, 1989.



