

Zeitschrift: Helvetica Physica Acta

Band: 49 (1976)

Heft: 5

Artikel: Crystal field effects on the elastic constants of single crystals of PrAl₂ and NdAl₂

Autor: Godet, M. / Purwins, H.-G.

DOI: <https://doi.org/10.5169/seals-114791>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. [Siehe Rechtliche Hinweise.](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. [Voir Informations légales.](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. [See Legal notice.](#)

Download PDF: 15.05.2025

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Crystal Field Effects on the Elastic Constants of Single Crystals of PrAl_2 and NdAl_2

by **M. Godet** and **H.-G. Purwins**

Université de Genève, Département de Physique de la Matière Condensée, 32, bd d'Yvoy,
1211 Genève 4, Switzerland

(2.VI.76)

Abstract. We report measurements of the sound velocity of single crystals of PrAl_2 and NdAl_2 between 4.2 K and 280 K. For the elastic constants we find at 280 K (in 10^{11} N/m²): $C_{11} = 1.382 \pm 1.2\%$; $C_{12} = 0.42 \pm 3.6\%$; $C_{44} = 0.452 \pm 1.0\%$ for PrAl_2 and $C_{11} = 1.41 \pm 1.2\%$; $C_{12} = 0.470 \pm 3.6\%$; $C_{44} = 0.429 \pm 1.0\%$ for NdAl_2 . Some modes of the sound velocity increase with increasing temperature over a large range above the Curie temperature. This increase is interpreted in terms of the interaction between the crystal field and the strains.

Introduction

The chemical and physical properties of the REAl_2 intermetallic compounds (RE = rare earth) are similar in many respects. All members of the series have the MgCu_2 Laves phase structure [1] and their melting points vary between 1370°C and 1500°C only [2, 3]. With the exception of EuAl_2 and YbAl_2 the REAl_2 compounds contain RE ions which are three valent. Detailed investigations of the crystal field in several of the REAl_2 compounds show that the 4th and 6th order terms change little from one RE to another [4]. Magnetization measurements demonstrate that most of the REAl_2 compounds order ferromagnetically (for a review on magnetic properties of polycrystals see Ref. [5], for single crystals see Ref. [4, 6–9]).

However measurements on the electronic specific heat [10] and the exchange interaction [6, 7] in some of the REAl_2 compounds reveal important deviations from the expected similarities. This is an indication for a change in the band structure and consequently in the chemical binding when replacing one rare earth by another. Under these circumstances it is interesting to investigate the elastic constants of the REAl_2 series in a systematic way because of their close connection to chemical binding. It is also of interest to look for the effect of the crystal field on the elastic constants.

Single crystal elastic constants of LaAl_2 and GdAl_2 [3, 11], TbAl_2 [12] and DyAl_2 (only two combinations) [13] are reported earlier. In the present work, we determine the elastic constants of single crystals of PrAl_2 and NdAl_2 in the temperature range from 4.2 K to 280 K. The temperature dependence of some elastic constants is analyzed in terms of the interaction between the crystal field and the strains. A comparison of the elastic constants of PrAl_2 and NdAl_2 with those of LaAl_2 , GdAl_2 , TbAl_2 and DyAl_2 does not show an obvious systematic behaviour.

Experimental Results

The REAl_2 compounds are prepared from 99.9% pure RE and 99.999% pure Al. Single crystalline cylinders with the axis parallel to $[110]$ and $[100]$ have been obtained by the Czochralski method [14]. By spark cutting and polishing we obtained samples of approximately 4 mm diameter and 3 to 9 mm length with faces parallel within 0.1μ . The misorientation was smaller than 1° . The room temperature densities of PrAl_2 and NdAl_2 were 5.013 ± 0.005 and $5.097 \pm 0.005 \text{ g/cm}^3$ which compare well with the theoretical densities of 5.0277 and 5.1682 g/cm^3 [15].

The elastic constants were determined by the ultrasonic technique using pulses of 10 MHz and 1μ sec. length. From 4.2 K to 35 K the temperature was measured with a germistor, for higher temperatures a copper-constantan thermocouple was used. The temperature was stabilized by an Artronix (Model 5301) temperature controller within 0.01 K. The absolute accuracy in the temperature read was of the order of $\pm 0.5 \text{ K}$ in the region from 25–45 K and $\pm 0.1 \text{ K}$ otherwise.

For the PrAl_2 and NdAl_2 we measured the sound velocities of the longitudinal and the transverse modes with propagation along $[100]$ and $[110]$. For all modes we observed considerable attenuation and in no case more than 14 echoes could be detected. One set of measurements of the sound velocities allowing for a determination of the complete set of C_{ik} 's is given in Figure 1 for PrAl_2 and in Figure 2 for NdAl_2 . The absolute error in the experimental sound velocities is of the order of $\pm 15 \text{ m/sec}$ and for the relative error we estimate $\pm 5 \text{ m/sec}$. In Table I and II we give the elastic constants C_{11} , C_{12} and C_{44} deduced from Figures 1 and 2.

Discussion

In Figures 1 and 2 we see that the sound velocities exhibit a sharp minimum at $T_c = (31.0 \pm 0.5) \text{ K}$ for PrAl_2 and at $T_c = (77.2 \pm 0.1) \text{ K}$ for NdAl_2 . These anomalies are due to the ferromagnetic-paramagnetic phase transition. The T_c value of PrAl_2 compares well with the result of specific heat measurements ($T_c = 31.8 \text{ K}$) [16] and is also in fair agreement with data obtained from neutron ($T_c = 34 \text{ K}$) [17] and magnetization ($T_c \approx 34 \text{ K}$ [18]; $T_c = 32 \text{ K}$ [19]) measurements. For NdAl_2 one deduces from specific heat data $T_c = 77.2 \text{ K}$ [16] and from magnetization data $T_c = 80 \text{ K}$ [18]. In view of the uncertainty of a Curie point determination in a neutron or magnetization experiment on materials like the REAl_2 compounds, we find good agreement between our T_c values and those reported in the literature.

In all measurements of the sound velocities of NdAl_2 we observe a broad maximum at 35 K and around 4.2 K a rather steep decrease with decreasing temperature accompanied by strong attenuation. Below 4 K no accurate measurement of the sound velocity was possible. However, for the C_{44} mode with propagation along $[100]$ we have evidence that saturation is obtained in the sound velocity around 1.2 K at a value which is roughly 10% below the 4.2 value.

A detailed discussion of the temperature dependence of the sound velocities in Figures 1 and 2 is difficult. In particular, this is the case in the ferromagnetic region because details of the domain structure are important. Above the Curie temperature, we separate the temperature dependence into two contributions. The first contribution comes from the crystal field and the second from all other effects, which do not contain the crystal field. As can be seen from LaAl_2 [11] the latter contribution is

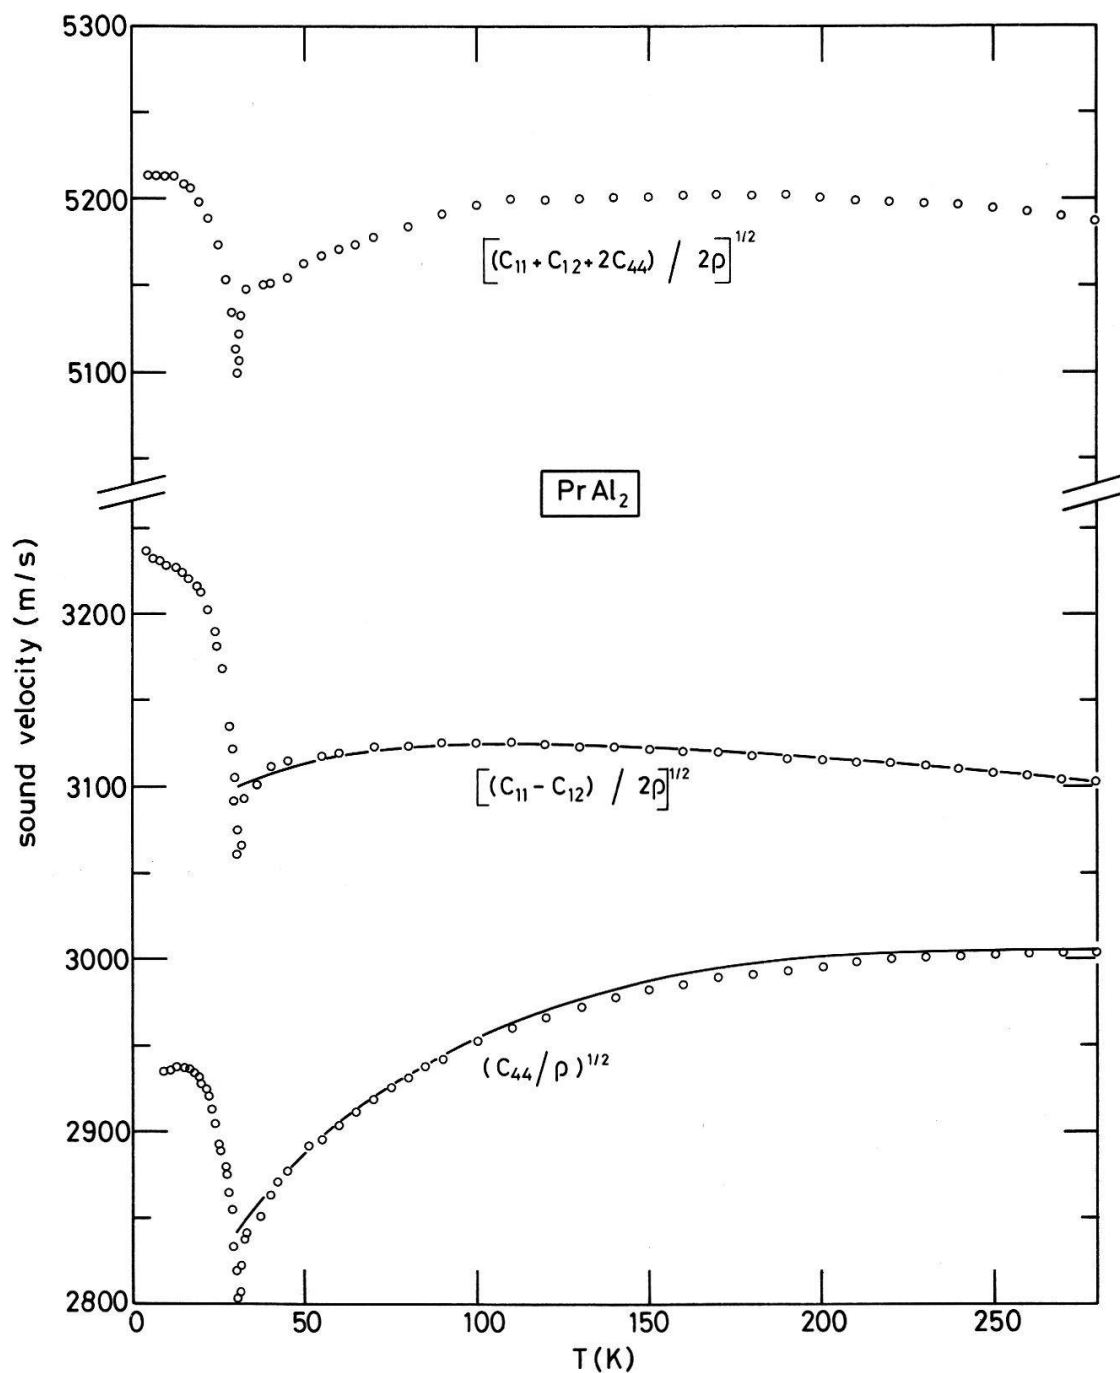


Figure 1

Experimental points and fitted curves of the sound velocities of PrAl_2 plotted as a function of temperature. The C_{44} mode is measured along $[100]$ the other modes along $[110]$.

approximately linear in temperature from 80 K to 280 K. We therefore write the temperature dependence of the elastic constants as [22]

$$C_{\Gamma} = C_{\Gamma}^0(1 - \alpha T)(1 - g_{\Gamma}^2 \chi_{\Gamma}(T)) \quad (1)$$

C_{Γ} is a combination of elastic constants specified by Γ . C_{Γ}^0 is a constant, α the temperature coefficient and g_{Γ}^2 the coupling parameter between the crystal field and the strains ε_{Γ} .

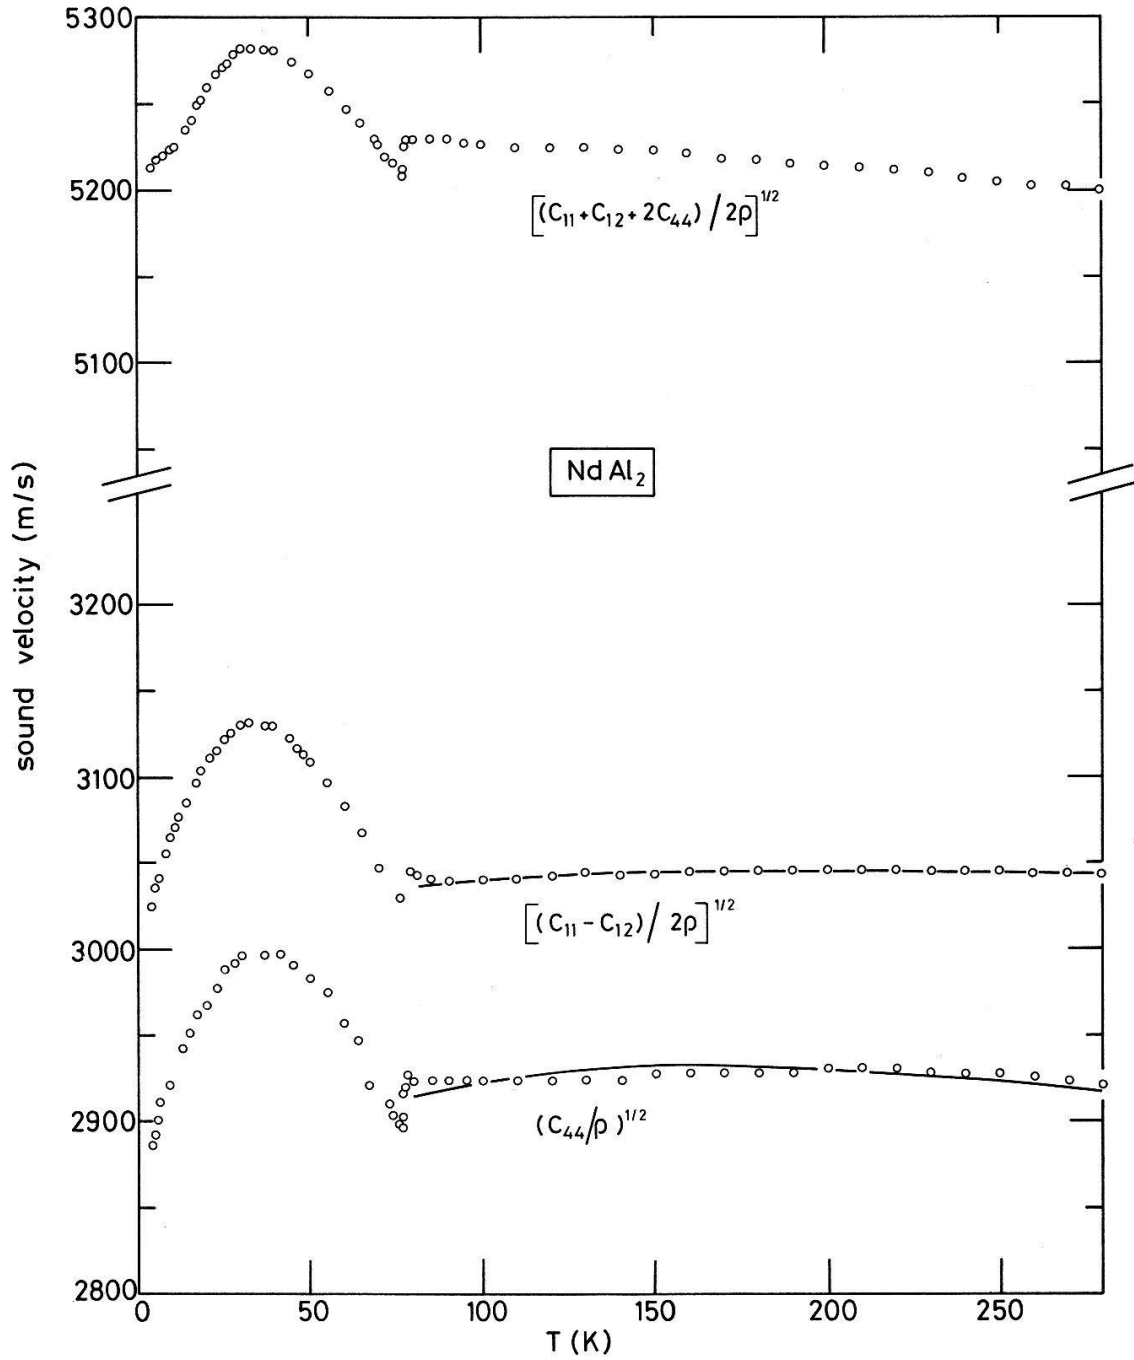


Figure 2

Experimental points and fitted curves of the sound velocities of NdAl_2 plotted as a function of temperature. The C_{44} mode is measured along $[100]$ the other modes along $[110]$.

To calculate $\chi_\Gamma(T)$ in equation (1) for $C_\Gamma = (C_{11} - C_{12})$ and $C_\Gamma = C_{44}$ we assume that the magnetoelastic Hamiltonian has the form [20, 21]

$$\begin{aligned}\hat{H}(C_{11} - C_{12}) &= -g_2(((C_{11}^0 - C_{12}^0)/N)(1 - \alpha_2 T))^{1/2} O_2^0 \cdot (2\varepsilon_{zz} - \varepsilon_{xx} - \varepsilon_{yy}) \\ \hat{H}(C_{44}) &= -g_3((C_{44}^0/N)(1 - \alpha_3 T))^{1/2} O_2^{-2} \cdot (2\varepsilon_{xy})\end{aligned}\quad (2)$$

Here N is the number of magnetic ions, ε_{ij} are the strains, O_l^m are the equivalent Stevens operators [22]. According to [23] χ_Γ can then be written as

Table 1
Elastic constants of PrAl₂

PrAl ₂			
<i>T</i> (°K)	<i>C</i> ₁₁ × (10 ¹¹ N/m ²)	<i>C</i> ₁₂ × (10 ¹¹ N/m ²)	<i>C</i> ₄₄ × (10 ¹¹ N/m ²)
4.2	1.455	0.406	0.431
10	1.453	0.408	0.431
20	1.443	0.409	0.429
31	1.400	0.462	0.394
40	1.404	0.434	0.410
50	1.406	0.433	0.418
60	1.407	0.432	0.423
70	1.407	0.430	0.427
80	1.407	0.430	0.430
90	1.406	0.428	0.434
100	1.406	0.428	0.437
110	1.406	0.428	0.439
120	1.406	0.429	0.441
130	1.406	0.429	0.443
140	1.405	0.428	0.444
150	1.403	0.427	0.445
160	1.401	0.426	0.446
170	1.400	0.425	0.447
180	1.400	0.426	0.448
190	1.399	0.426	0.449
200	1.398	0.425	0.450
210	1.397	0.425	0.450
220	1.395	0.424	0.451
230	1.393	0.423	0.451
240	1.389	0.420	0.451
250	1.387	0.419	0.452
260	1.386	0.419	0.452
270	1.384	0.419	0.452
280	1.382	0.418	0.452

$$\chi_{\Gamma} = (1/Z) \left\{ \sum_n \exp(-E_n/KT) |V_{\Gamma nn}|^2 / KT - 2 \sum_{n>m} [\exp(-E_m/KT) - \exp(-E_n/KT)] (E_m - E_n)^{-1} |V_{\Gamma n, m}|^2 \right\} \quad (3)$$

where V_{Γ} is O_2^0 and O_2^{-2} respectively, Z is the partition function and E_m , E_n the eigenvalues of the ground state of the free RE^{3+} ion experiencing a cubic crystalline field [24]. To calculate the E_m , E_n and the matrix elements $V_{\Gamma nm}$ we use the crystal field parameters obtained from magnetization measurements on PrAl₂ and NdAl₂ [4]. We remark that χ_{Γ} is always positive.

To obtain the calculated sound velocities $v_{\Gamma} = (C_{\Gamma}/\rho)^{1/2}$ for the $(C_{11} - C_{12})$ - and the C_{44} -mode we choose C_{Γ}^0 , α and g_{Γ}^2 to obtain good agreements of equation 1 with experiment. The results of the fits are given for α and g_{Γ}^2 in Table I, and for the sound velocities in Figures 1 and 2 (as a full line). We note that deviations from a 'LaAl₂ like' temperature dependence are well described by the calculated curves above the Curie temperature.

Table 2
Elastic constants of NdAl₂

NdAl ₂			
T (°K)	C_{11} $\times (10^{11} \text{ N/m}^2)$	C_{12} $\times (10^{11} \text{ N/m}^2)$	C_{44} $\times (10^{11} \text{ N/m}^2)$
4.2	1.469	0.544	0.366
10	1.421	0.471	0.433
20	1.440	0.464	0.445
30	1.451	0.461	0.453
40	1.450	0.460	0.454
50	1.441	0.464	0.450
60	1.429	0.469	0.442
70	1.420	0.481	0.430
77.2	1.409	0.481	0.424
80	1.418	0.482	0.432
90	1.417	0.483	0.432
100	1.415	0.481	0.432
110	1.415	0.481	0.432
120	1.415	0.480	0.432
130	1.415	0.480	0.432
140	1.415	0.479	0.432
150	1.413	0.477	0.433
160	1.413	0.476	0.433
170	1.411	0.474	0.433
180	1.411	0.472	0.433
190	1.410	0.473	0.433
200	1.408	0.471	0.434
210	1.408	0.470	0.434
220	1.407	0.469	0.434
230	1.407	0.470	0.433
240	1.405	0.468	0.433
250	1.405	0.467	0.432
260	1.407	0.470	0.429
270	1.406	0.470	0.430
280	1.406	0.470	0.428

In Figure 3, we compare the room temperature bulk modulus $(C_{11} + 2C_{12})/3$, the shear modulus $(C_{11} - C_{12})/2$ and the anisotropy $(C_{11} - C_{12})/2C_{44}$ of different REAl₂ compounds. We see that the represented elastic parameters have no simple systematic behaviour as might have been expected from the similarity of many of the physical properties.

Conclusion

In the present work, we see that the temperature dependences of the elastic constants of PrAl₂ and NdAl₂ show strong crystal field effects. In some cases these effects dominate the usual LaAl₂ like temperature dependence and lead to a fairly large increase of the elastic constants with increasing temperature. Qualitatively we were able to give a correct description of these crystal field effects. However, from Table III, we see that the values of α vary considerably when comparing LaAl₂, PrAl₂ and NdAl₂. We conclude therefore that either the values of α are simply very

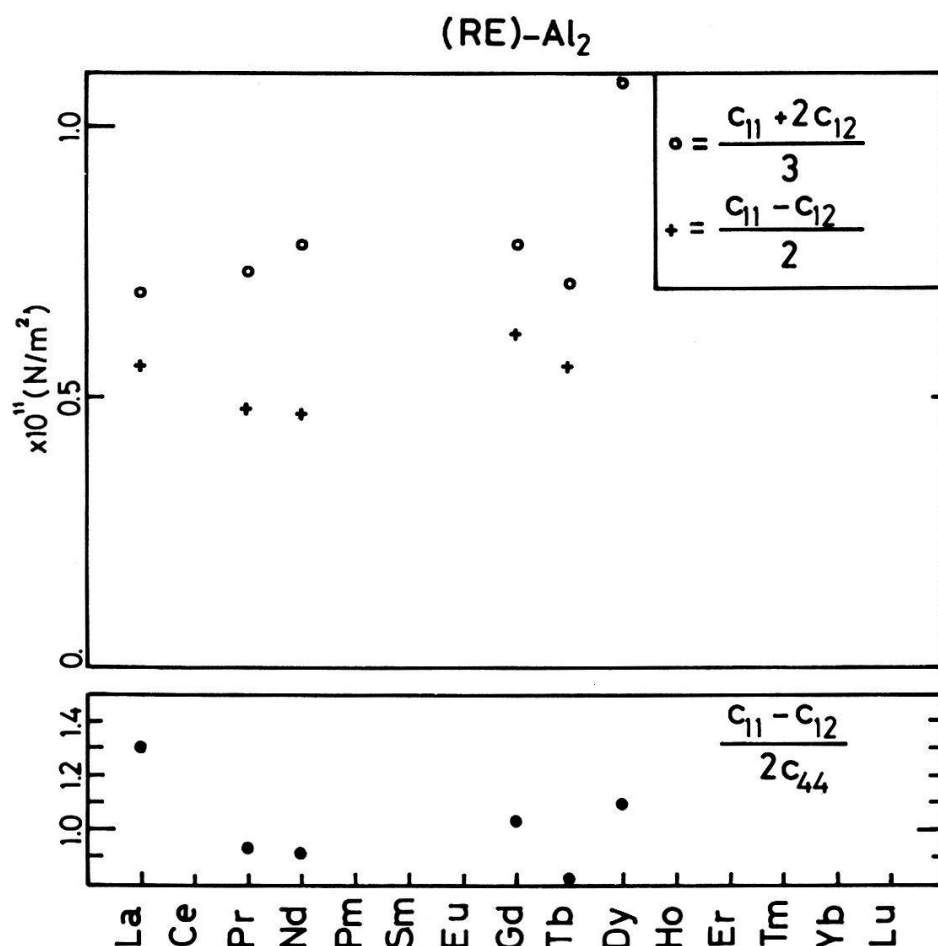


Figure 3

Bulk modulus $(C_{11} + 2C_{12})/3$, shear modulus $(C_{11} - C_{12})/2$ and anisotropy $(C_{11} - C_{12})/2C_{44}$ of some REAl_2 compounds at room temperature. The data for LaAl_2 and GdAl_2 are taken from Ref. [11], those of TbAl_2 and DyAl_2 from Ref. [12] and [13].

	$C_{11} - C_{12}$		C_{44}	
	$\alpha(10^{-5} \text{ }^\circ\text{K})$	$g_T^2(10^{-3} \text{ }^\circ\text{K})$	$\alpha(10^{-5} \text{ }^\circ\text{K})$	$g_T^2(10^{-3} \text{ }^\circ\text{K})$
PrAl_2	14.0	4.9	18.4	41.7
NdAl_2	3.0	2.5	20.3	12.4
LaAl_2	16.4	—	5.7	—

Table 3

Parameters α and g_T^2 describing the temperature dependence of elastic constants of REAl_2 compounds according to equation (1). The values of LaAl_2 are taken from Ref. [11].

different from one REAl_2 to another, or that α contains also magneto-elastic contribution so that equation (3) is only a qualitative expression for the effect of the crystal field on the elastic constants.

From the systematic comparison of the bulk modulus, the shear modulus and the anisotropy in Figure 3, we conclude that no simple systematic behaviour is followed. From the investigation of elastic constants we therefore believe that the lattice forces and the chemical binding vary considerably throughout the series even though these compounds are very similar in many other respects.

Acknowledgements

Very stimulating discussions with Prof. B. Lüthi are greatly acknowledged. We wish to thank Mr. R. Cartoni for preparing the drawings.

This work is supported by the Fonds National Suisse de la Recherche Scientifique.

REFERENCES

- [1] J. H. WERNICK and S. GELLER, *Trans. AIME* 218, 866–8 (1960).
- [2] K. H. BUSCHOW and J. H. N. VAN VUCHT, *Z. Metallk.* 57, 162–6 (1966).
- [3] R. J. SCHILTZ, Thesis, Iowa State Univ. Ames Iowa (1972).
- [4] H.-G. PURWINS, E. WALKER, B. BARBARA, M. F. ROSSIGNOL, A. FURRER, *J. Phys. C9*, 1025–30 (1976).
- [5] N. R. TAYLOR, *Adv. Phys.* 20, 551–660 (1971);
W. E. WALLACE, *Rare Earth Intermetallics*, Academic Press, New York, London (1973).
- [6] W. BÜHRER, M. GODET, H.-G. PURWINS and E. WALKER, *Solid State Commun.* 13, 881–4 (1973).
- [7] J. G. HOUMANN, P. BAK, H.-G. PURWINS and E. WALKER, *J. Phys. C7*, 2691–6 (1974).
- [8] H.-G. PURWINS, W. J. L. BUYERS, T. HOLDEN and E. C. SVENSSON, *Proc. Int. Conf. MMM – Philadelphia 1975*, to be published.
- [9] H.-G. PURWINS, E. WALKER, B. BARBARA, M. F. ROSSIGNOL and P. BAK, *J. Phys. C7*, 3573–82 (1974).
- [10] R. E. HUNGSBERG and K. A. GSCHNEIDER, *J. Phys. Chem. Solids* 33, 401–7 (1972).
- [11] R. J. SCHILTZ and J. F. SMITH, *J. Appl. Phys.* 45, 4681–5 (1974).
- [12] M. GODET, *Helvetica Physica Acta* 46, 770–1 (1974).
- [13] G. DUBLON, H. KLIMKER, U. ATZMONY, M. P. DARIEL, M. ROSEN, A. GRAYEWSKI and D. FEKETE, *Phys. Lett.* 53A, 23–4 (1975).
- [14] M. GODET, E. WALKER and H.-G. PURWINS, *J. Less Common Metals* 30, 301–2 (1973).
- [15] I. R. HARRIS, R. C. MANSEY and G. V. RAYNOR, *J. Less Common Metals* 9, 270–80 (1965).
- [16] C. DEENADAS, A. W. THOMPSON, R. S. CRAIG and W. E. WALLACE, *J. Phys. Chem. Solids* 32, 1853–66 (1971).
- [17] N. NERESON, C. OLSEN and G. ARNOLD, *J. Appl. Phys.* 39, 4605–9 (1968).
- [18] H. J. WILLIAMS, J. H. WERNICK, E. A. NESBITT and R. C. SHERWOOD, *J. Phys. Soc. Japan* 17, Suppl. B-I, 91–95 (1962).
- [19] B. BARBARA, M. F. ROSSIGNOL, H.-G. PURWINS and E. WALKER, *Coll. Int. C.N.R.S. No. 242*, 'Physique sous champs magnétiques intenses', 51–56.
- [20] E. R. CALLEN and H. B. CALLEN, *Phys. Rev.* 129, 578–93 (1963).
- [21] B. LÜTHI, M. E. MULLEN, K. ANDRES, E. BUCHER and J. P. MAITA, *Phys. Rev. B8*, 2639–48 (1973).
B. LÜTHI, M. E. MULLEN and E. BUCHER, *Phys. Rev. Lett.* 31, 95–8 (1973).
- [22] K. W. H. STEVENS, *Proc. Phys. Soc. A65*, 209–15 (1952).
- [23] P. M. LEVY, *J. Phys. C6*, 3545–56 (1973).
- [24] K. R. LEA, M. J. M. LEASK and W. P. WOLF, *J. Phys. Chem. Solids* 23, 1381–405 (1962).