

Zeitschrift: Schweizerische mineralogische und petrographische Mitteilungen =
Bulletin suisse de minéralogie et pétrographie

Band: 47 (1967)

Heft: 1: Feldspäte

Artikel: Preliminary single-crystal study of the lattice angles of triclinic feldspars
at temperatures up to 1200°C

Autor: Grundy, H.D. / Brown, W.L.

DOI: <https://doi.org/10.5169/seals-36928>

Nutzungsbedingungen

Die ETH-Bibliothek ist die Anbieterin der digitalisierten Zeitschriften. Sie besitzt keine Urheberrechte an den Zeitschriften und ist nicht verantwortlich für deren Inhalte. Die Rechte liegen in der Regel bei den Herausgebern beziehungsweise den externen Rechteinhabern. [Siehe Rechtliche Hinweise.](#)

Conditions d'utilisation

L'ETH Library est le fournisseur des revues numérisées. Elle ne détient aucun droit d'auteur sur les revues et n'est pas responsable de leur contenu. En règle générale, les droits sont détenus par les éditeurs ou les détenteurs de droits externes. [Voir Informations légales.](#)

Terms of use

The ETH Library is the provider of the digitised journals. It does not own any copyrights to the journals and is not responsible for their content. The rights usually lie with the publishers or the external rights holders. [See Legal notice.](#)

Download PDF: 22.01.2025

ETH-Bibliothek Zürich, E-Periodica, <https://www.e-periodica.ch>

Preliminary Single-Crystal Study of the Lattice Angles of Triclinic Feldspars at Temperatures up to 1200°C

By *H. D. Grundy* and *W. L. Brown* (Manchester)*)

With 5 figures in the text and 2 tables

Abstract. The reciprocal lattice angles of six plagioclases and a maximum microcline were measured at a series of temperatures up to 1200°C on a Buerger precession camera. The crystals were mounted by sintering on a thermocouple without cement and heated in a gas flame.

The angles of the plagioclases change smoothly with temperature, α^* changing most and β^* least; the angles of microcline do not change with temperature. Plots of the change of α^* against γ^* for a sequence of temperatures are straight lines; the effect of heat on these angles for low and high-albite is similar to the effect of the substitution of potassium on the angles measured at room temperature.

The feldspars have been extensively studied at room temperature, but until recently little was known about their properties at elevated temperatures. The change in the lattice angles of anorthite with temperature is known from early optical work (RINNE, 1914; SCHNAASE, 1936 — see also Figs. 4 and 5) and expansion measurements have been made on various feldspars using dilatometric methods (KÔZU and UEDA, 1933). The first systematic X-ray study at elevated temperatures was made by MACKENZIE (1952) on albite-rich feldspars — he measured the angular separation of the lines 111 and $1\bar{1}1$ on diffraction charts as a function of temperature. Since then lattice angles for albite and anorthite and complete parameters for a basic labradorite at elevated temperatures have been published (BROWN, 1962; GUBSER et al., 1963; STEWART et al., 1966), and lattice parameters for two plagioclases have been discussed

*) Department of Geology, The University, Manchester 13, England.

Present addresses: Department of Geology, MacMaster University, Hamilton, Ontario, and Laboratoire de Minéralogie et Cristallographie, 1 rue Victor-Cousin, Paris 5e respectively.

(STEWART and VON LIMBACH, 1964). BLOSS (1964) determined the change of extinction angle with temperature in anorthite.

During this preliminary study, single crystals of plagioclase feldspars selected from material of known composition and a microcline were examined on a Buerger precession camera. Each crystal was mounted on a Pt/Pt-13%Rh thermocouple by sintering at temperatures below

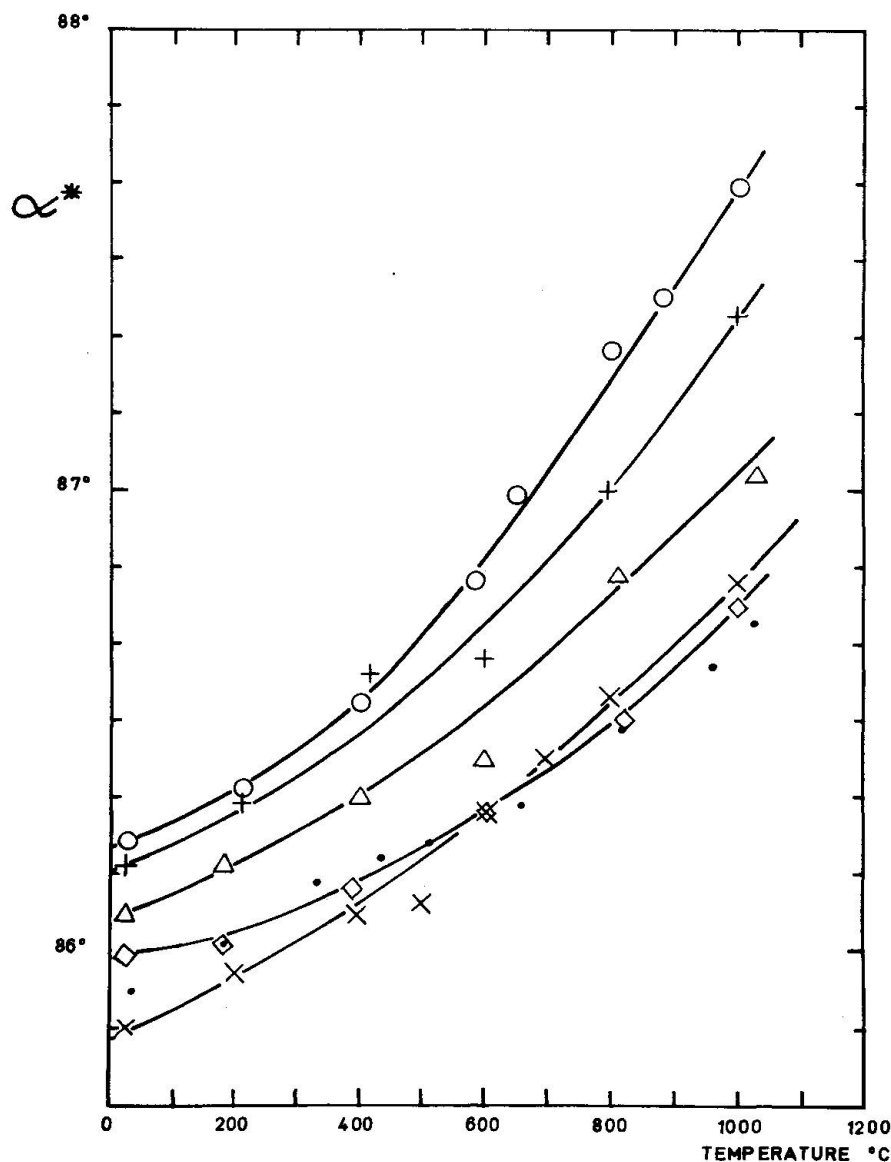


Fig. 1. Plot of α^* against temperature for all plagioclases except anorthite: \circ albite, F9; $+$ oligoclase, F44; \triangle andesine, E24; \diamond labradorite, F70; \times bytownite, F71. The symbol \bullet is for material similar to F70 from same locality calculated from data given by STEWART et al. (1966). Anorthite has not been plotted because of overlap, see Fig. 4.

their melting points (usually 1100°C) for 10–30 mins. in an R.F. heater. This method of mounting avoided the use of cement which might have produced compositional changes in the crystals. The crystals were heated in a coalgas/nitrogen/air or coalgas/oxygen flame (for temperatures in the ranges 100–700°C and 700–1500°C respectively) similar to that described by GUBSER et al. (1963). With the exception of F 70 two crystals of each feldspar were mounted, with which a-, b- and c-axis precession photographs were taken ($\mu = 15^\circ$, Mo $K\alpha$). Room-temperature photographs were taken before and after mounting by sintering and also after completion of the high-temperature photographs — no significant changes occurred in the lattice angles. The photographs at high tempera-

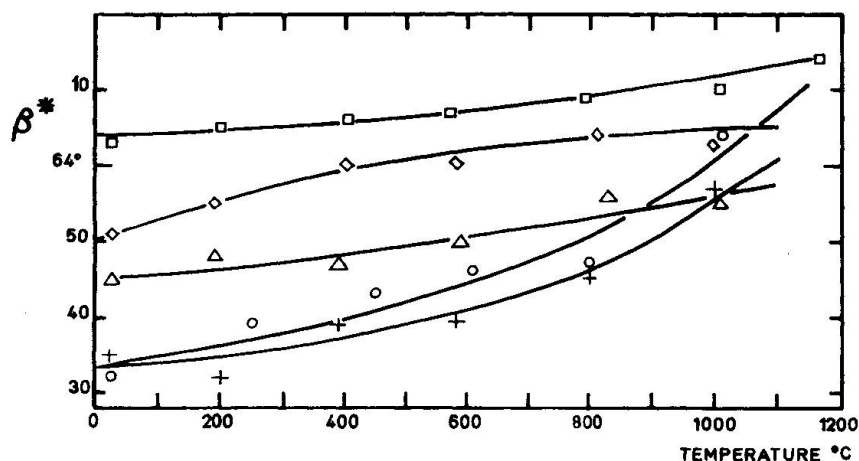


Fig. 2. Plot of β^* against temperature for all plagioclases: symbols as in Fig. 1, and, in addition, \square anorthite, F 72.

ture were generally taken using high-speed Polaroid film to reduce exposure time to 5–10 mins. and hence the total period of heating. The reciprocal lattice angles α^* , β^* , γ^* were measured directly from the precession photographs and are accurate to within $\pm 5'$, except for microcline where the accuracy is $\pm 10'$ due to lineage. The temperatures are accurate to $\pm 30^\circ\text{C}$ in the range 200–400°C and $\pm 10^\circ\text{C}$ in the range 400–1200°C.

The materials studied are shown in Table 1 and their lattice angles at different temperatures given in Table 2 and depicted in Figs. 1–5. As can be seen from Figs. 1–4, the variation of the reciprocal lattice angles with temperature is smooth within experimental error in all cases. STEWART et al. (1966) have suggested that there are discontinuities in the curve of molecular volume against temperature for a calcic labradorite

from Lake County, Oregon, but no such discontinuities could be detected in the plots of α^* and γ^* against temperature for material from the same locality (F 70). The values of these angles calculated from the data of STEWART et al. are also plotted in Figs. 1, 3 and 5, from which the great

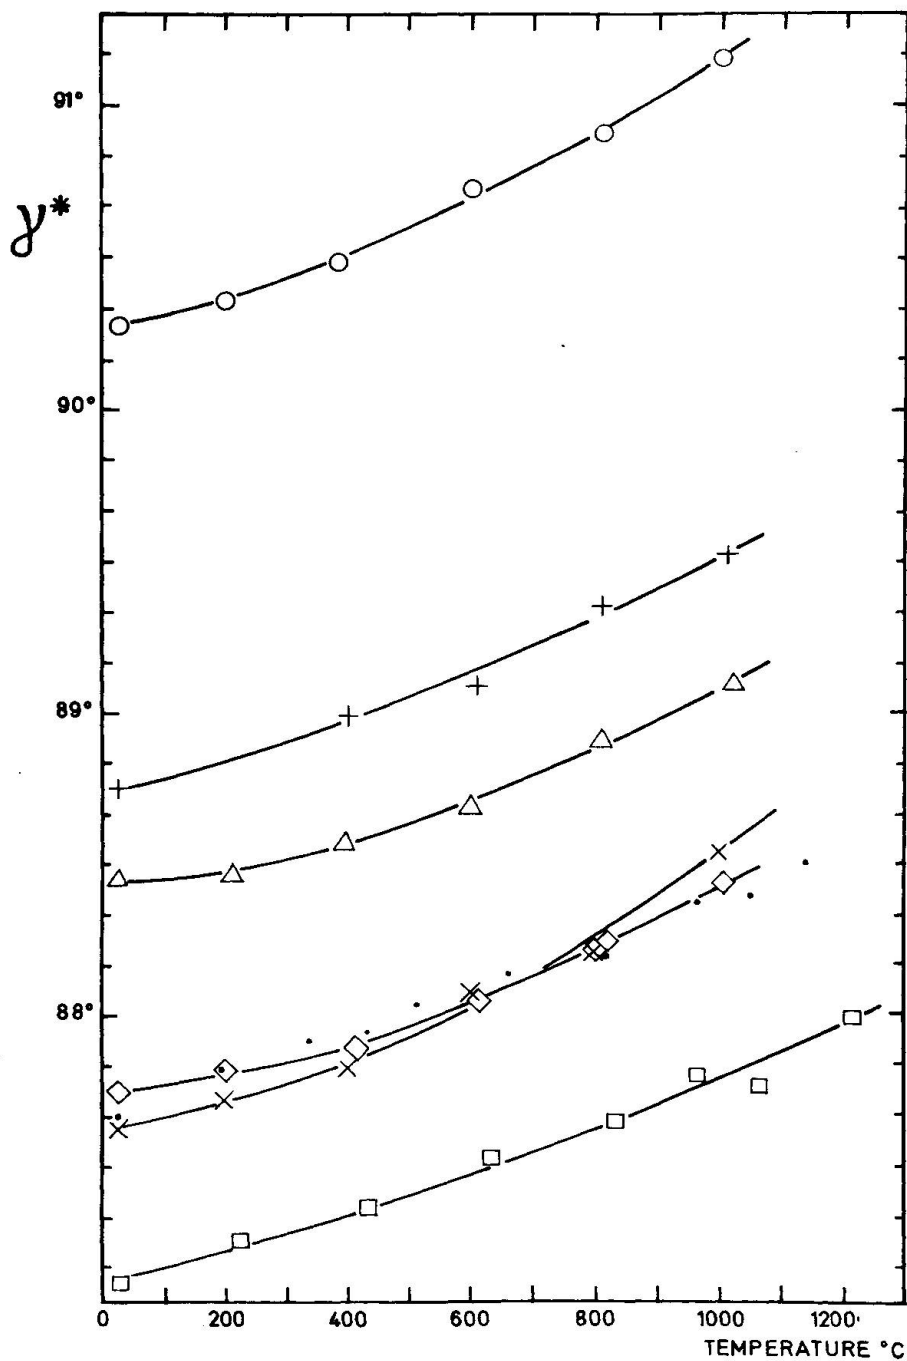


Fig. 3. Plot of γ^* against temperature for all plagioclases, symbols as in Figs. 1 and 2.

similarity of results is apparent. The exposure times were not long enough to determine whether the b-reflections were present or absent.

For all plagioclases the angle α^* changes most with temperature, γ^* slightly less and β^* very much less (Figs. 1—4). The effect of temperature on all three angles is greatest for low-albite and decreases progressively with increasing anorthite content. F 71 is exceptional in that the changes in these angles with temperature (especially α^*) are greater than for plagioclases of similar composition — the b-reflections were present and sharp at room temperature but were so much weaker at higher temperatures that it was not possible to tell whether they were absent or not. The lattice angles of microcline do not change with temperature within experimental error (Table 2).

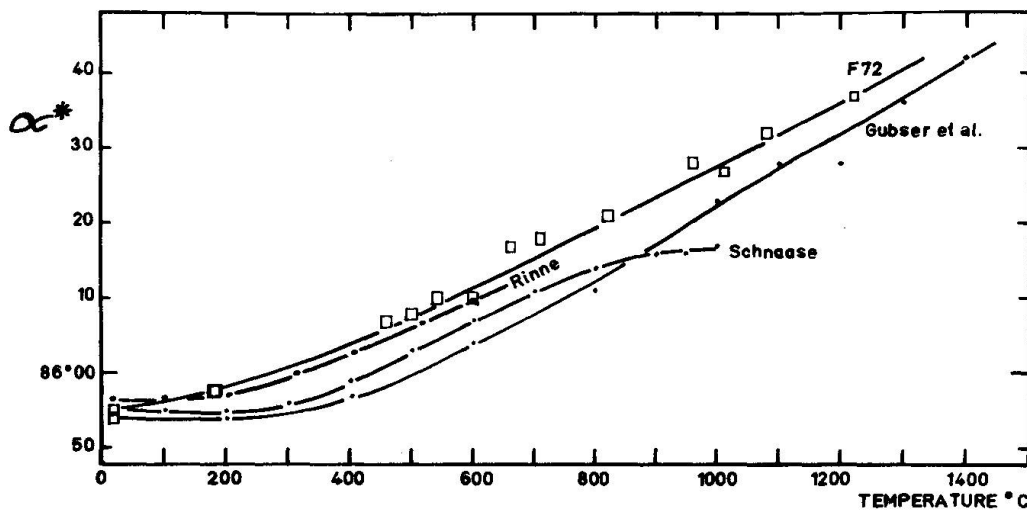


Fig. 4. Plot of α^* against temperature for anorthite F 72 and data from literature.
□ F 72.

Fig. 4 is a plot of α^* against temperature for F 72 and for published data on anorthite by RINNE (1914), SCHNAASE (1936) and GUBSER et al. (1963). The values for α^* at elevated temperature are consistently greater for F 72 than those given by GUBSER et al. for ostensibly the same material though they agree with those of RINNE; this may be due to slightly different composition or structural state or both. The c-reflections of unheated material from F 72 are strong and only slightly diffuse on photographs taken at room temperature but are diffuse at room temperature after mounting by heating to 1350—1400°C for 30 mins. They become diffuse on raising the temperature and are absent on photographs taken at 400°C or above (compare BROWN et al., 1963). The noteworthy lack of change in α^* between -170°C and about 300°C (RINNE, 1914

and Fig. 4) may be connected with the disappearance of the c-reflections. The b-reflections remain sharp and strong on all photographs at temperatures up to 1220°C, so that anorthite becomes and remains body-centred up to that temperature. No sign of flattening of the curve of α^* against temperature above 900°C was found by us or by GUBSER et al. — the flattening found by SCHNAASE between 900—1000°C (Fig. 4) may be due to different material or inaccurate temperature determination.

Fig. 5 is a plot of α^* against γ^* for temperatures at 200 degree intervals read from the smooth curve in Figs. 1—4. The variation of α^* against γ^* with temperature is linear or nearly so for all plagioclases;

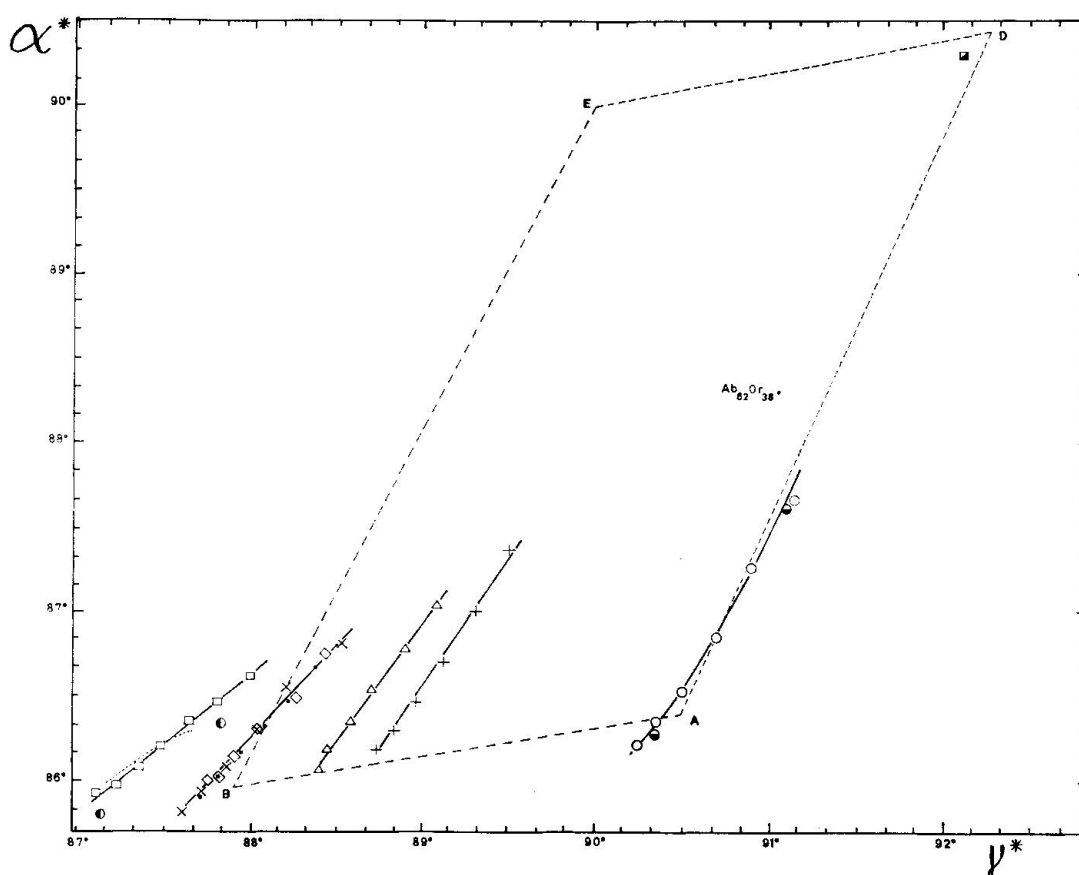


Fig. 5. Plot of α^* against γ^* at 200 degree intervals: from below 26, 200, 400, 600, 800, 1000°C (and 1200°C in case of anorthite). Same symbols as Figs. 1 and 2. Data for labradorite from STEWART et al. (1966) as Figs. 1 and 3. ☺ albite S 502 from BROWN (1962) at 25 and 1000°C. ● anorthite from Miyake Jima, Japan, at 25 and 1000°C (approximate composition An_{90}). ■ average value for microcline, 400. The values at the corners of the parallelogram ABDE from MACKENZIE and SMITH (1962). $Ab_{62}Or_{38}$ from GOLDSMITH and LAVES (1961). Dotted curve ... data from SCHNAASE (1936).

microcline shows no changes in these angles with temperature. The slopes of the lines for the plagioclases are roughly parallel to the line for the anorthoclases (high-albite—sanidine join) at room temperature (MACKENZIE and SMITH 1955; BROWN 1960). The slopes decrease slightly with increasing anorthite contents. The line for low-albite is of such slope that a continuation would lead to microcline (cf. BROWN, 1962, p. 362). The effect of increasing temperature on α^* and γ^* of low-albite is similar to the effect on these angles at room temperature of substitution of potassium in low-albite (the metastable low-albite—microcline series, GOLDSMITH and LAVES, 1961), a temperature rise of 1000°C producing about the same change as the substitution of about 30% Or (Fig. 5). The effect on α^* and γ^* of high-albite on increasing the temperature is also similar to that of substituting about 30—40% Or (MACKENZIE 1952, LAVES 1952).

Table 1

| No. | Feldspar | Composition in wt. % | | | Rock type | Locality |
|------|-------------------------------|----------------------|-------|------|----------------|--------------------------------------|
| | | An | Ab | Or | | |
| F 9 | Albite ¹⁾ | 0.15 | 99.26 | 0.59 | Alpine vein | Schyn-Schlucht, Grisons, Switzerland |
| F 44 | Oligoclase ²⁾ | 28.2 | 69.3 | 2.5 | Pegmatite | Bakersville, Mitchell Co., N. C. |
| E 24 | Andesine ³⁾ | 49.0 | 47.2 | 3.8 | Anorthosite | Essex County, N. Y. |
| F 70 | Labradorite ^{2), 4)} | 67.5 | 31.6 | 0.9 | Lava | Lake View, Oregon |
| F 71 | Bytownite ²⁾ | 75.7 | 23.7 | 0.6 | Anorthosite | Crystal Bay, Minnesota |
| F 72 | Anorthite ^{2), 5)} | 95.4 | 3.1 | 1.5 | Cavity in Lava | Vesuvius, Italy |
| 400 | Microcline ⁶⁾ | not analysed | | | Pegmatite | Anjanabiana |

¹⁾ Analysis by WEIBEL (1958), see also BROWN (1960).

²⁾ Analysis by E. TAYLOR and H. D. GRUNDY.

³⁾ Sample from EMMONS et al. (1953), new no. 9.

⁴⁾ Similar material to that used by STEWART et al. (1966).

⁵⁾ S 140, same sample as used by BROWN et al. (1963) and by GUBSER et al. (1963).

⁶⁾ Sample not analysed because of presence of exsolved albite. Albite-free specimens were chosen from thin sections for single-crystal work.

Table 2

F 9, Albite from Schyn-Schlucht, Grisons, Switzerland. An_{0.15}

| T °C | α^* | T °C | β^* | T °C | γ^* |
|-----------------|------------|------|-----------|------|------------|
| 25 ¹ | 86° 20' | 25 | 63° 34' | 25 | 90° 16' |
| 25 ² | 86 17 | 25 | 63 33 | 25 | 90 16 |
| 25 ³ | 86 16 | 25 | 63 32 | 25 | 90 16 |
| 210 | 86 22 | 250 | 63 39 | 200 | 90 21 |
| 400 | 86 32 | 450 | 63 43 | 380 | 90 28 |
| 585 | 86 48 | 610 | 63 46 | 600 | 90 43 |
| 700 | 86 59 | — | — | — | — |
| 800 | 87 18 | 800 | 63 47 | 810 | 90 54 |
| 880 | 87 25 | — | — | — | — |
| 1000 | 87 39 | 1010 | 64 04 | 1000 | 91 09 |

F 44, Oligoclase from Bakersville, N. C. An₂₈

| T °C | α^* | T °C | β^* | T °C | γ^* |
|-----------------|------------|------|-----------|------|------------|
| 26 ¹ | 86° 11' | 26 | 63° 36' | 26 | 88° 45' |
| 26 ² | 86 10 | 26 | 63 34 | 26 | 88 46 |
| 26 ³ | 86 11 | 26 | 63 35 | 26 | 88 45 |
| 210 | 86 19 | 200 | 63 32 | — | — |
| 415 | 86 36 | 390 | 63 39 | 400 | 88 59 |
| 600 | 86 38 | 580 | 63 39 | 610 | 89 05 |
| 795 | 87 00 | 800 | 63 45 | 810 | 89 21 |
| 990 | 87 22 | 1000 | 63 57 | 1010 | 89 31 |

E 24, Andesine from Essex Co., N. Y. An₄₉

| T °C | α^* | T °C | β^* | T °C | γ^* |
|-----------------|------------|------|-----------|------|------------|
| 26 ¹ | 86° 02' | 26 | 63° 46' | 26 | 88° 27' |
| 26 ² | 86 10 | 26 | 63 45 | 26 | 88 23 |
| 26 ³ | 86 05 | 26 | 63 44 | 26 | 88 27 |
| 180 | 86 11 | 190 | 63 48 | 210 | 88 28 |
| 400 | 86 20 | 390 | 63 47 | 390 | 88 34 |
| 600 | 86 25 | 590 | 63 50 | 600 | 88 41 |
| 810 | 86 49 | 830 | 63 56 | 810 | 88 55 |
| 1030 | 87 02 | 1010 | 63 55 | 1020 | 89 06 |

F 70, Labradorite from Lake View, Oregon. An₆₈

| T °C | α^* | T °C | β^* | T °C | γ^* |
|-----------------|------------|------|-----------|------|------------|
| 26 ¹ | 85° 59' | 26 | 63° 50' | 26 | 87° 49' |
| 26 ² | 86 00 | 26 | 63 51 | 26 | 87 45 |
| 26 ³ | 86 00 | 26 | 63 51 | 26 | 87 45 |
| 180 | 86 01 | 190 | 63 55 | 200 | 87 49 |
| 390 | 86 08 | 400 | 64 00 | 410 | 87 53 |
| 600 | 86 18 | 580 | 64 00 | 610 | 88 03 |
| 820 | 86 30 | 810 | 64 04 | 800 | 88 13 |
| 1000 | 86 45 | 1000 | 64 03 | 1000 | 88 26 |

F 71, Bytownite from Crystal Bay, Minnesota. An₇₆

| T °C | α^* | T °C | β^* | T °C | γ^* |
|-----------------|------------|--------------|-----------|------|------------|
| 26 ¹ | 85° 51' | not measured | | 26 | 87° 37' |
| 26 ² | 85 51 | „ | | 26 | 87 40 |
| 26 ³ | 85 50 | „ | | 26 | 87 37 |
| 200 | 85 57 | „ | | 200 | 87 43 |
| 400 | 86 05 | „ | | 400 | 87 49 |
| 500 | 86 06 | „ | | — | — |
| 600 | 86 18 | „ | | 600 | 88 04 |
| 700 | 86 25 | „ | | — | — |
| 800 | 86 33 | „ | | 800 | 88 12 |
| 1000 | 86 44 | „ | | 1000 | 88 32 |

F 72, Anorthite from Vesuvius, Italy. An₉₅

| T °C | α^* | T °C | β^* | T °C | γ^* |
|-----------------|------------|------|-----------|------|------------|
| 26 ¹ | 85° 55' | 26 | 64° 00' | 26 | 87° 09' |
| 26 ² | 85 54 | 26 | 64 03 | 26 | 87 07 |
| 26 ³ | 85 55 | 26 | 64 03 | 26 | 87 07 |
| 180 | 85 57 | 200 | 64 05 | 220 | 87 16 |
| 460 | 86 07 | 405 | 64 06 | 430 | 87 22 |
| 500 | 86 08 | — | — | — | — |
| 540 | 86 10 | — | — | — | — |
| 600 | 86 10 | 570 | 64 07 | 630 | 87 32 |
| 660 | 86 17 | — | — | — | — |
| 710 | 86 18 | — | — | — | — |
| 820 | 86 21 | 795 | 64 09 | 830 | 87 39 |
| 960 | 86 28 | — | — | 960 | 87 48 |
| 1000 | 86 26 | — | — | — | — |
| 1010 | 86 27 | 1010 | 64 10 | — | — |
| 1080 | 86 32 | — | — | 1060 | 87 46 |
| 1220 | 86 37 | 1170 | 64 14 | 1210 | 87 59 |

400, Microcline from Anjanabiana

| T °C | α^* | T °C | β^* | T °C | γ^* |
|-----------------|------------|------|-----------|------|------------|
| 25 ¹ | 90° 19' | 25 | 64° 05' | 25 | 92° 17' |
| 25 ² | 90 19 | 25 | 64 03 | 25 | 92 12 |
| 25 ³ | 90 19 | 25 | 64 08 | 25 | 92 07 |
| 180 | 90 16 | — | — | — | — |
| 400 | 90 21 | — | — | 400 | 92 06 |
| 600 | 90 21 | 570 | 63 58 | 580 | 92 04 |
| 800 | 90 17 | 800 | 64 04 | 800 | 92 06 |
| 1020 | 90 16 | 1000 | 64 07 | 1010 | 92 00 |

1. Unheated specimen
2. Mounted specimen
3. Specimen on completion of high-temperature photography

REFERENCES

- BLOSS, F. D. (1964): Optical extinction of anorthite at high temperatures. *Amer. Min.* 49, 1125—1131.
- BROWN, W. L. (1960): Lattice changes in heat-treated plagioclases — the existence of monalbite at room temperature. *Z. Kristallogr.* 113, 297—329.
- (1962): Peristerite unmixing in the plagioclases and metamorphic facies series. *Norsk Geol. Tidsskr.* 42, 354—382.
- BROWN, W. L., HOFFMANN, W. and LAVES, F. (1963): Über kontinuierliche und reversible Transformationen des Anorthits (CaAl₂Si₂O₈) zwischen 25 und 350°C. *Natw.* 50, 221.
- EMMONS, R. C. (editor) (1953): Selected petrogenic relationships of plagioclase. *Geol. Soc. Amer., Memoir* 52, 1—142.

- GOLDSMITH, J. R. and LAVES, F. (1961): The sodium content of microcline and the microcline-albite series. Instituto „Lucas Mallada“ C.S.I.C. (España), *Cursillos y conferencias*, VIII, 81—96.
- GUBSER, R. A., HOFFMANN, W. and NISSEN, H. U. (1963): Röntgenaufnahmen mit der Buergerschen Präzessionskamera bei Temperaturen zwischen 1000°C und 2000°C. *Z. Krist.* 119, 264—272.
- KÔZU, S. and UEDA, J. (1933): Thermal expansion of plagioclase. *Proc. Imperial Acad. Japan*, 9, 262—264.
- LAVES, F. (1952): The phase relations of the alkali feldspars. *J. Geol.* 60, 549—574.
- MACKENZIE, W. S. (1952): The effect of temperature on the symmetry of high-temperature soda-rich feldspars. *Amer. J. Sci., Bowen vol.*, 319—342.
- MACKENZIE, W. S. and SMITH, J. V. (1955): The alkali feldspars I. Orthoclase-micropertthites. *Amer. Min.* 40, 707—732.
- (1962): Single-crystal X-ray studies of crypto- and micro-perthites. *Norsk Geol. Tidsskr.*, 42, 72—103.
- RINNE, F. (1914): Die Kristallwinkelveränderung verwandter Stoffe beim Wechsel der Temperatur. *Zbl. Mineral. Geol. Paläont.*, 705—718, esp. 711—718.
- SCHNAASE, H. (1936): Über die Änderung des Achsenverhältnisses und der Lage des rhombischen Schnittes mit der Temperatur beim Anorthit vom Vesuv. *Z. Krist.* 93, 444—463.
- STEWART, D. B. and VON LIMBACH, D. (1964): Thermal expansion of NaAlSi₃O₈ and calcic labradorite (abstract). *Trans. Amer. Geophys. Union*, 45, 126—127.
- STEWART, D. B., WALKER, G. W., WRIGHT, T. L. and FAHEY, J. J. (1966): Physical properties of calcic labradorite from Lake County, Oregon. *Amer. Min.* 51, 177—197.
- WEIBEL, M. (1958): Chemische Untersuchungen an Albiten aus den Schweizer Alpen. *Schweiz. Min. Petr. Mitt.* 38, 61—75.

Manuscript received June 30th, 1966.